



Cite this: DOI: 10.1039/d1nj01986d

# Controlled reduction of aromaticity of alkylated polyaromatic compounds by selective oxidation using $\text{H}_2\text{WO}_4$ , $\text{H}_3\text{PO}_4$ and $\text{H}_2\text{O}_2$ : a route for upgrading heavy oil fractions†

 Ewa Nowicka,<sup>a</sup> Meenakshisundaram Sankar,<sup>a</sup> Robert L. Jenkins,<sup>a</sup> David W. Knight,<sup>a</sup> David J. Willock,<sup>a</sup> Graham J. Hutchings,<sup>a</sup> Manuel Francisco<sup>‡b</sup> and Stuart H. Taylor<sup>‡\*</sup>

Heavy crude oil fractions which form the residues from fractional distillation are a significant proportion of current hydrocarbon reserves. However, processing residues for use as chemicals or fuels is hampered by the high polyaromatic content of this material. Selective reduction of aromaticity by targeted ring opening and the preservation of alkylated chain side groups are key requirements for the upgrading of alkylated polynuclear aromatic hydrocarbons (PAHs) to more easily processed and higher value molecules. In this study, a  $\text{H}_2\text{WO}_4$  catalyst combined with  $\text{H}_3\text{PO}_4$  and  $\text{H}_2\text{O}_2$  oxidant is applied to the selective oxidation of PAHs containing different lengths of substituent alkylated chain, and different numbers of rings in the fused aromatic core. For a model substrate of 2-ethylnaphthalene, using traditional organic solvents, aliphatic carbon was oxidized more readily compared to aromatic carbon. However, it was found that the oxidation to desired products can be specifically controlled as the selectivity is directed by the choice of solvent, with reactions carried out in acetonitrile giving oxidation only in the aromatic region of the molecule. With larger polyaromatic molecules, a biphasic solvent system is used with Aliquat 336 as a phase transfer agent. Even for this more complex reaction system high conversion to the corresponding alkylated ring opened compounds was obtained.

 Received 23rd April 2021,  
Accepted 13th July 2021

DOI: 10.1039/d1nj01986d

[rsc.li/njc](http://rsc.li/njc)

## 1. Introduction

Heavy crude oil fractions, residues and bitumens represent between 4 wt% and 16 wt% of current processed crude oil across global production sites.<sup>1</sup> As such, this represents a significant and largely under-used feedstock in the petrochemicals industry. Currently, these fractions can only be used in low value applications such as binders for road surfaces and as a waterproofing adhesive in construction. The use of this complex mix of high molecular weight compounds through further upgrading to higher value products would help maximise productivity and enable us to meet an increasing demand for fuels without developing a large number of new reserves.<sup>2</sup> The petroleum industry uses three major methods for upgrading: deep oil fluid catalytic cracking, thermal cracking, including

delayed coking and hydrocracking with desulfurization. Fluid catalytic cracking converts a high boiling feedstock to more useful petroleum compounds, with the use of high temperature, moderate pressure, and most importantly a fluidized powdered catalyst. Thermal cracking and delayed coking uses no catalyst or additional chemicals to achieve cracking at very high temperatures (450–470 °C).<sup>3,4</sup> Hydrocracking on the other hand requires high pressure hydrogen, which can result in over-cracking and formation of low value gas.<sup>5</sup> A very low selectivity and high energy demand are the major drawbacks for all these methods.

Oxidation offers a more facile route for petroleum residue transformation, and potentially could become a core technology. These heavy fractions consist mostly of alkylated polynuclear aromatic hydrocarbons, (PAHs), so the challenge is to control the oxidation of aromatic carbon whilst preserving alkyl chain side groups.<sup>6–9</sup> The fact that PAH molecules are difficult to oxidise is apparent when it is realised that they are also a major component of anthropogenic atmospheric pollution from combustion and industrial activity.<sup>10</sup> Their chemical removal in this context is also an area of intense research but with the goal of complete reaction to  $\text{CO}_2$  and water. We have recently reported that Ruthenium Ion Catalyzed Oxidation (RICO) of alkylated PAH molecules can have

<sup>a</sup> Cardiff Catalysis Institute, School of Chemistry, Cardiff University, Main Building, Park Place, Cardiff, CF10 3AT, UK. E-mail: nowicka@cardiff.ac.uk,

taylorsh@cardiff.ac.uk

<sup>b</sup> ExxonMobil Research & Engineering Company, 1545 Route 22 East, Annandale, New Jersey 08801, USA

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d1nj01986d

‡ Deceased March 9, 2016.



the required selectivity for residue processing.<sup>11</sup> RICO chemistry finds a wide range of applications in C–H bond activation and oxygen transfer reactions.<sup>12</sup> By judicious choice of experimental conditions and solvent system we were able to demonstrate oxidation of aromatic regions of model alkylated PAH compounds, whilst aliphatic carbons were unreacted.<sup>13</sup> In RICO chemistry RuCl<sub>3</sub> is transformed into a RuO<sub>4</sub> oxidising species using NaIO<sub>4</sub> as oxidant. The high oxidation state RuO<sub>4</sub> moiety shows a strong affinity for double bonds in the aromatic system of PAH molecules that are chemically isolated, *i.e.* regioselectivity favours the formation of a [3+2] intermediate in positions that lead to minimal loss of aromaticity.<sup>14</sup> This provides a route to selectively oxidise aromatic carbon producing predominantly aldehyde and carboxylic acid functionality. However, this ruthenium-based catalytic system relies on an expensive metal and requires a strong oxidant which produces a stoichiometric equivalent of salt waste, therefore a cheaper catalyst and more environmentally benign oxidant would be preferred.

As early as 1959, Payne and Williams demonstrated that a combination of a tungsten based catalyst with H<sub>3</sub>PO<sub>4</sub> and H<sub>2</sub>O<sub>2</sub> as oxidant can give a highly selective oxidative catalytic system for organic synthesis.<sup>15</sup> This system later became known as the Ishii-Venturello oxidation system.<sup>16,17</sup> This combination of relatively cheap catalyst and high efficiency oxidant has been reported to be active for the oxidation of alcohols,<sup>18</sup> aldehydes,<sup>19</sup> olefins,<sup>16</sup> as well as aromatic hydrocarbons.<sup>20,21</sup> A number of studies have been published demonstrating the use of W containing compounds as oxidation catalysts, for example as Keggin type polyoxometalates.<sup>22,23</sup> However, tungsten in the form of H<sub>2</sub>WO<sub>4</sub> is a more potent oxidation catalyst, mediating the conversion of PAH molecules such as phenanthrene and pyrene to the corresponding diacids when combined with H<sub>3</sub>PO<sub>4</sub> and using H<sub>2</sub>O<sub>2</sub> as oxidant.<sup>20,24</sup> The use of hydrogen peroxide as the primary oxidant is also attractive as it removes the production of salt waste that would occur with the RICO approach. These observations suggest that aqueous H<sub>2</sub>WO<sub>4</sub>/H<sub>2</sub>O<sub>2</sub> could be suitable for selective oxidation of alkylated-PAHs to reduce aromaticity. However, oxidation of alkylated PAH molecules is more challenging than the parent PAH compounds exemplified by phenanthrene and pyrene. It is known that the  $\alpha$ -carbon, the first aliphatic carbon bound to the aromatic system, is potentially more susceptible to oxidation than the aromatic core itself due to the relatively low C–H bond energy for carbon atoms in the benzyl position. To date there are no studies to establish the influence of alkyl substituents in the oxidation of alkylated-PAH substrates with this catalyst system.

The high molecular weight alkylated PAH molecules found in residues are very hydrophobic requiring a non-polar solvent. In contrast, a polar solvent is needed for the H<sub>2</sub>O<sub>2</sub> oxidant and H<sub>2</sub>WO<sub>4</sub> catalyst so that reactions will usually take place in a biphasic system. While this has advantages in terms of product separation<sup>25</sup> it can also result in poor mixing between the substrate and oxidising species. Reaction efficiency can be improved using a phase transfer catalyst and the addition of an acid. Barrio *et al.*<sup>26</sup> have combined experimental findings and theoretical calculations to propose that oxidation in this case begins with the reaction of H<sub>2</sub>WO<sub>4</sub> with H<sub>2</sub>O<sub>2</sub> to form an

anionic bisperoxotungstate complex in the aqueous phase. This complex reacts further with phosphonic acid, to give a form that can be transported *via* the phase transfer catalyst to the organic phase, where oxidation of the substrate takes place. Following substrate oxidation, the monoperoxo tungstate ion moves back to the aqueous layer where it can again react with H<sub>2</sub>O<sub>2</sub> to reform the anion and the cycle repeats itself.

Herein, we investigate the use of the H<sub>2</sub>WO<sub>4</sub>/H<sub>2</sub>O<sub>2</sub> catalytic system for the oxidation of a range of alkylated polynuclear aromatic hydrocarbons, as model compounds for upgrading of crude oil residues. For larger molecules we employ a biphasic solvent system with phase transfer agent to improve catalytic efficiency. Our fundamental focus is to examine oxidation catalysed by H<sub>2</sub>WO<sub>4</sub> as an alternative to the previously discussed RICO Chemistry.

## 2. Experimental

### 2.1. Oxidation reactions

**Oxidation of 2-ethylnaphthalene.** Oxidation reactions were carried out in a glass reactor over the temperature range 65 °C to 85 °C in a range of solvents: C<sub>6</sub>H<sub>5</sub>Cl, C<sub>6</sub>H<sub>5</sub>CH<sub>3</sub>, C<sub>2</sub>H<sub>5</sub>CN and CH<sub>3</sub>CN. The reaction mixture was stirred using a magnetic bar inside the reactor (700 rpm). In a typical reaction the round bottom flask was firstly charged with the 2-ethylnaphthalene (18.8 mmol) and the desired solvent (8 ml). The catalyst (H<sub>2</sub>WO<sub>4</sub>, 0.614 mmol), 10% H<sub>3</sub>PO<sub>4</sub> (0.14 ml) and Aliquat 336 (0.24 ml) were subsequently added, and the reaction mixture left to stir for 2 min. H<sub>2</sub>O<sub>2</sub> (30%, 12 ml, 118 mmol) was then added dropwise under continuous stirring, the flask containing the reaction mixture was then transferred to a preheated oil bath and was fitted with a water-cooled condenser. For quantitative analysis, samples (0.2 ml) were withdrawn from the organic layer at the desired time interval and mixed with an external standard, 2-butanol (20  $\mu$ l) prior to GC analysis. To enable the withdrawal of the sample, stirring was stopped until visible separation between the two phases was seen. Samples for GC analysis were then withdrawn from both organic and aqueous layers and were analyzed quantitatively using a Varian 450 Gas Chromatograph with a VF-5ht (30 m, 0.25 mm) column and a FID detector.

It is believed that after 6 hours reaction, no oxidant remained in the reaction mixture as it was either consumed in the oxidation reaction or alternatively decomposed.

**Oxidation of PAHs with long alkyl chains and <sup>1</sup>H NMR analysis.** NMR analysis of PAHs with long alkyl chains required clean <sup>1</sup>H NMR spectra, which were dependent on the use of Aliquat 336, as the phase transfer catalyst masks signals from products in the aliphatic region of the <sup>1</sup>H NMR. This was achieved by lowering the concentration of Aliquat 336 in a scaled down experiment. Oxidation reactions were carried out in a glass reactor for 16 hours, unless otherwise stated. First, substrate (0.1 mmol) was dissolved in toluene (1 ml), then H<sub>2</sub>WO<sub>4</sub> (0.019 g, 0.077 mmol), H<sub>3</sub>PO<sub>4</sub> (10% 0.01 ml) and Aliquat 336 (0.0012 g, solution in toluene) were added and mixed together. In the last step of the reaction H<sub>2</sub>O<sub>2</sub> 30% (2 ml, 20 mmol) was added under continuous



stirring. The reaction was run at a temperature of 80 °C. After the required time of reaction (16 h), the two phases were separated, and the toluene phase was washed with water (3 × 20 ml). The aqueous phase was washed with toluene (3 × 20 ml) and the organic and aqueous filtrates were combined with the organic or aqueous layer. The organic phase was dried over anhydrous Na<sub>2</sub>SO<sub>4</sub>, the solid removed by filtration and the filtrate evaporated to dryness. The aqueous phase was also evaporated to dryness. CDCl<sub>3</sub> (0.7 ml) was added to the flask containing the organic products and a 0.6 ml portion of the resultant solution was transferred to the NMR tube fitted with an internal standard sealed glass insert (1%TMS in CDCl<sub>3</sub>). Residues from the aqueous layer were dissolved in D<sub>2</sub>O and analyzed using the <sup>1</sup>H NMR technique. However, no products were detected in the aqueous layer. The <sup>1</sup>H NMR spectra obtained were compared against the spectra of the pure substrate, which was previously prepared by dissolving 0.1 mmol of compound in 0.6 ml of CDCl<sub>3</sub>. The <sup>1</sup>H NMR spectrum of this solution was recorded in the presence of the same internal standard glass insert. The protons of interest which are used to calculate the percentage of preserved alkyl chain are protons A in the side chain that are α to the aromatic ring and protons D which are terminal protons (Fig. S1, ESI†). These protons were chosen for calculations, as the methylene protons of the aliphatic carbon, which are attached to the aromatic ring, will produce a triplet that is highly susceptible to any changes at the point of attachment of the aliphatic chain to the aromatic ring. This triplet signal was used for the quantification of the oxidation products in which the aliphatic chains remained intact (Protons A). The electronic environment of the terminal H in a long-chain alkyl substituent of a polyaromatic compound will be affected to a lesser extent by changes due to the oxidation of the polyaromatic region, than will the protons in the ethyl group of 2-ethylnaphthalene. Consequently, the terminal protons were used as an internal standard for the quantification of the products of long chain alkyl aromatics using <sup>1</sup>H NMR spectroscopy (Protons D).

Comparison of the integrated areas for protons A and D between the 0 and X h samples gives a measure of the percentage of products in which the aliphatic chain remains intact. The detailed methodology of analysing <sup>1</sup>H NMR peaks using this technique has been described in a separate publication.<sup>11</sup> An example of a <sup>1</sup>H NMR spectrum used for the calculation of percentage of preserved alkyl chain is shown in Fig. S1 (ESI†).

In the oxidation of 9-octadecylphenanthrene, the following conditions were used. First the substrate (0.043 g, 0.1 mmol) was dissolved in C<sub>6</sub>H<sub>5</sub>Cl (3 ml), H<sub>2</sub>WO<sub>4</sub> (0.038 g, 0.154 mmol), H<sub>3</sub>PO<sub>4</sub> (10% 0.02 ml) and Aliquat 336 (0.0024 g in toluene) were added and stirred for a few minutes. Subsequently H<sub>2</sub>O<sub>2</sub> (50%, 4 ml, 65 mmol) was added dropwise. The reaction was performed at 110 °C. Post reaction analysis steps were the same as above.

Conversion in oxidation reactions of 2-nonylphenanthrene, 9-octadecylphenanthrene and 2-octadecylpyrene was determined using GC, according to the methodology described above for 2-ethylnaphthalene.

**Competitive oxidation reactions.** In the competitive oxidation study, 0.247 mmol of each substrate (non-alkylated compounds) or 0.256 mmol (alkylated-compounds) were dissolved in C<sub>6</sub>H<sub>5</sub>Cl

(8 ml). The catalyst (H<sub>2</sub>WO<sub>4</sub>, 0.025 mmol), 10% H<sub>3</sub>PO<sub>4</sub> (0.14 ml) and Aliquat 336 (0.24 ml) were subsequently added and the reaction mixture stirred for 2 min. H<sub>2</sub>O<sub>2</sub> (30%, 2.5 ml, 25 mmol) was then added dropwise under continuous stirring, the flask containing the reaction mixture was then transferred to a pre-heated oil bath and was fitted with a water-cooled condenser and stirred vigorously whilst it was maintained at 80 °C. Quantitative analysis was performed in a similar way to that used for the oxidation of 2-ethylnaphthalene.

## 2.2. Product analysis

<sup>1</sup>H NMR, <sup>13</sup>C NMR and 2D NMR spectra were recorded on a Bruker DPX 500 MHz instrument. For <sup>13</sup>C NMR and 2D NMR analysis, firstly the solvent used in the reaction was evaporated, the sample was then placed under vacuum until it was completely dry and a volume of approx. 1 ml of deuterated solvent added to the dry residue to dissolve it. The solution (0.5–0.7 ml) was subsequently transferred to the NMR tube for analysis.

Gas Chromatography–Mass Spectrometry (GC-MS) analysis was performed using a Waters GCT premier instrument fitted with an Agilent HP-5MS column. Unless otherwise stated in the earlier part of the experimental section, samples were analyzed as received from the reaction mixture. A sample of 1 ml of reaction mixture (from both or single solvent layer) was transferred to a GC-MS vial and analyzed without further treatment.

Mass Spectrometry analysis (MS) was performed using a Waters LCT Premier XE (ES), while EI data was generated using a Waters GCT Premier EI (EI) instrument. Similarly to GC-MS analysis, samples were analyzed after the reaction was completed. A volume of approximately 1 ml was transferred to a GCMS vial and analyzed without further treatment.

Infrared (IR) analysis were performed using a Jasco FT/IR-660 spectrometer. Compounds dissolved in dichloromethane solution were deposited on the surface of a NaCl plate. The film formed on the plate was analysed directly.

## 3. Results and discussion








### 3.1. Oxidation of 2-ethylnaphthalene

Since our aim was to investigate the selectivity trends for alkylated aromatics, this study focused primarily on 2-ethylnaphthalene, (1), as it is a simple alkylated polynuclear aromatic compound with the advantage that monophasic and biphasic solvent environments can be compared. In previous reports we have shown that the oxidation of 2-ethylnaphthalene using RICO chemistry leads to oxidation of the aromatic carbon region of the molecule, whilst there was little or no oxidation of the alkyl side chain.<sup>11</sup> This observation was independent of the solvent system used, as in both monophasic and biphasic solvent systems aromatic carbons were predominantly oxidized. In this work, a range of solvents, which differ in their polarity index,<sup>27</sup> were evaluated for oxidation of 2-ethylnaphthalene using H<sub>2</sub>WO<sub>4</sub>/H<sub>2</sub>O<sub>2</sub> and the main products observed are presented in Table 1.

Oxidation of 2-ethylnaphthalene using a biphasic system with toluene as the organic solvent (the lowest polarity index)



Table 1 Products of 2-ethylnaphthalene oxidation in a range of solvents

Entry	Organic solvent	Polarity index <sup>a</sup> ( $\epsilon_r$ )	React. T <sup>b</sup> /°C	Con. <sup>c</sup> /%	Major products
1	Toluene C <sub>6</sub> H <sub>5</sub> CH <sub>3</sub>	2.4 (2.38)	80	30	 91% <b>2</b>
2	Chlorobenzene C <sub>6</sub> H <sub>5</sub> Cl	2.7 (5.62)	80	52	 37% <b>2</b>  16% <b>3</b>
3	Propionitrile C <sub>2</sub> H <sub>5</sub> CN	3.9 (27.7)	75	16	 42% <b>4</b>
4	Acetonitrile CH <sub>3</sub> CN	5.8 (37.5)	65	12	 15% <b>3</b>  54% <b>5</b>  21% <b>6</b>

Note: <sup>a</sup>  $\epsilon_r$  = dielectric constant. <sup>b</sup> Reaction temperature. <sup>c</sup> Conversion. Reaction conditions: 2-ethylnaphthalene 18.8 mmol, H<sub>2</sub>WO<sub>4</sub> 0.153 g (0.614 mmol), H<sub>2</sub>O<sub>2</sub> 35% 12 ml (137 mmol), Aliquat 336 0.24 ml, H<sub>3</sub>PO<sub>4</sub> 10% 0.14 ml, Solvent 8 ml, t = 6 h.

resulted in formation of acetophenone, (2), with high selectivity (91%, Table 1, entry 1, Fig. S2, ESI<sup>†</sup>), alongside other minor products. This shows that in a biphasic system with very different solvent polarities oxidation of the  $\alpha$ -carbon of the ethyl side chain of the molecule is the preferred reaction pathway.

When chlorobenzene is used as the organic phase solvent, GC-MS analysis (Fig. S3, ESI<sup>†</sup>), shows the formation of two major products (Table 1, entry 2); acetophenone, (2), 37% and 5-ethyl phthalic acid anhydride, (3), 16%, suggesting that both aromatic and aliphatic carbon can be oxidized.

The oxidation of 2-ethylnaphthalene with propionitrile as the organic solvent of the biphasic reaction mixture was carried out at a lower temperature than those used for the less polar solvents (75 °C *cf.* 80 °C), due to its lower boiling point. A notably lower conversion is seen compared to the toluene and chlorobenzene systems and the major product, naphthalene-2-yl-ethanol (4), is only oxidized at the  $\alpha$ -carbon of the alkyl chain. No acetophenone was detected (Table 1, entry 3 and Fig. S4, ESI<sup>†</sup>), as would be expected from the further oxidation of (4).

The highest polarity solvent considered for the organic phase was acetonitrile (Table 1, entry 4 and Fig. S5, ESI<sup>†</sup>). Acetonitrile has been previously reported to have a positive influence on the selectivity in RICO chemistry,<sup>28</sup> and so it was investigated in more detail for this new work with H<sub>2</sub>WO<sub>4</sub>/H<sub>2</sub>O<sub>2</sub>. The high polarity index of acetonitrile meant that attempts to use it as the organic solvent led to a monophasic reaction mixture and its low boiling point (82 °C) required the reaction temperature to be further reduced to 65 °C. A range of products were formed from 2-ethylnaphthalene oxidation using H<sub>2</sub>WO<sub>4</sub>/H<sub>2</sub>O<sub>2</sub> in acetonitrile. The major products were: 5-ethyl phthalic acid anhydride (3),

6-ethylnaphthalene-1,4-dione (5) and 6-ethyl-2-hydroxynaphthalene-1,4-dione (6), all of these preserved the ethyl chain, with only one aromatic ring oxidized as confirmed by <sup>13</sup>C NMR analysis of the product mixture. Indeed, a comparison of <sup>13</sup>C NMR spectra for the product mixture following 20 h of reaction with that of a pure standard of 2 showed no peak corresponding to the ketone group of acetophenone (2). This is the expected alkyl oxidation product that had been observed for reaction in toluene and chlorobenzene following oxidation at the  $\alpha$ -carbon of the alkyl side chain (Fig. S6, ESI<sup>†</sup>). This observation suggests that acetonitrile can provide a solvent environment able to direct oxidation to the aromatic region. These results differ from previously reported oxidation of 2-ethylnaphthalene in acetonitrile, as products in which unreacted and oxidized ethyl chain products were observed. However, that earlier study used tungsten polyoxometalates rather than tungstic acid and also employed a different ratio of substrate, catalyst and oxidant.<sup>22</sup>

The selectivity for the reaction catalysed with H<sub>2</sub>WO<sub>4</sub>/H<sub>2</sub>O<sub>2</sub> also differed significantly from the oxidation of 2-ethylnaphthalene using RICO chemistry. RICO gave a range of products for which the unreacted ethyl chain was observed (*e.g.* phthalaldehyde, isobenzofuran-1,3-dione, 5-ethylisobenzofuran-1,3-dione).<sup>11</sup> In our RICO work, selectivity was not affected by the choice of solvent for 2-ethylnaphthalene oxidation (CH<sub>3</sub>CN, H<sub>2</sub>O or CH<sub>3</sub>CN, DCM, H<sub>2</sub>O).<sup>11,14</sup> However, it was shown that, using RICO, the solvent affects the selectivity for oxidation of molecules with three or more aromatic rings, giving a lower degree of aliphatic carbon oxidation in the presence of acetonitrile.<sup>13</sup>

A possible explanation for the change of selectivity with solvent for 2-ethylnaphthalene using the H<sub>2</sub>WO<sub>4</sub>/H<sub>2</sub>O<sub>2</sub> system



could be the distribution of the tungsten complex in the reaction medium. Introduction of acetonitrile allows the reaction to occur in a single homogeneous phase, presumably improving mixing of the catalyst, substrate and oxidant. The bisperoxotungstate complex, that forms initially from reaction of  $\text{H}_2\text{WO}_4$  with  $\text{H}_2\text{O}_2$ , can more easily move through the reaction medium without the need for a phase transfer agent. A similar observation was reported by Noyori *et al.*<sup>29</sup> Tungsten is reduced as the substrate is oxidised, and so, once it has oxidized the C=C or C-H bond in a biphasic system the tungsten complex has to transfer back to the aqueous phase. In the monophasic system provided by acetonitrile the additional phase transfer steps are eliminated.<sup>30</sup> Even so, the use of acetonitrile as a solvent raises a problem of substrate solubility for higher molecular weight alkylated PAH molecules and limits the reaction temperature in an open reaction vessel because of the relatively low solvent boiling point. Therefore, for the more general problem of residue upgrading, the use of non-polar solvents is difficult to avoid. To address this point, further experiments with alkylated aromatic hydrocarbons containing more fused aromatic rings were performed in chlorobenzene.

### 3.2. Oxidation of polyaromatics with larger aromatic systems and longer alkyl chains

Various factors, such as the size of the aromatic ring system and substitution pattern of alkyl substituted PAHs can influence the regioselectivity in oxidation reactions between the aromatic and aliphatic regions of the molecule.<sup>31</sup> In our studies we focus not only on the effect of aromatic system size, but also on understanding how different substituent chain lengths and substitution positions influence the selectivity of the reaction.

Three different compounds were chosen for this study, the substituted three ring PAH molecules; 2-nonylphenanthrene (**7**) and 9-octadecylphenanthrene (**8**), and the substituted four ring system 2-octadecylpyrene (**9**). To determine the selectivity of the oxidation reaction between aromatic and aliphatic regions, the  $^1\text{H}$  NMR quantification methodology developed previously and summarised in the Experimental section, was applied (Fig. S1, ESI $^\dagger$ ).<sup>11</sup>

Table 2 summarises the conversion and proportion of preserved aliphatic hydrogen for each of the substrates. It is clear that conversion is dependent upon the number of fused aromatic rings present in the substrate, with higher conversion for the larger ring system of 2-octadecylpyrene (**9**). The alkyl chain length has relatively little influence on the conversion as **7** and **8** show

**Table 2** Effect of alkyl chain length, and position and number of aromatic rings on the activity and selectivity for oxidation of polyaromatic compounds oxidized using  $\text{H}_2\text{WO}_4/\text{H}_2\text{O}_2$

Substrate	Conversion/%	Preserved aliphatic H/%
2-Nonylphenanthrene, ( <b>7</b> )	48	78
9-Octadecylphenanthrene, ( <b>8</b> )	46	40
2-Octadecylpyrene, ( <b>9</b> )	95	93

Reaction conditions: substrate 0.1 mmol,  $\text{H}_2\text{WO}_4$  0.019 g (0.077 mmol),  $\text{H}_2\text{O}_2$  35% 2 ml (22.8 mmol), Aliquat 336 0.002 g (in 1 ml  $\text{C}_6\text{H}_5\text{CH}_3$  solution),  $\text{H}_3\text{PO}_4$  10% 0.01 ml,  $\text{C}_6\text{H}_5\text{Cl}$  3 ml,  $T = 80^\circ\text{C}$ ,  $t = 16$  h.

very similar values. However, comparison of the measured percentage preserved aliphatic hydrogen for substrates **7** and **8** does suggest that the location of the alkyl chain plays a crucial role in reaction selectivity. Aliphatic carbon at position 9 of the aromatic phenanthrene system in **8** is more susceptible to oxidation than carbon at position 2 of the same aromatic system (standard atom numberings are shown in Fig. S7, ESI $^\dagger$ ). It has been found from DFT calculations for the RICO oxidation system, that positions 9 and 10 in the phenanthrene ring system are the most energetically favourable positions for oxidation as the removal of these carbons from the aromatic system has only a limited effect on the resonance structures available.<sup>14</sup> The  $\alpha$ -carbon of an alkyl chain substituted at these positions is likely to be placed close to the oxidant making it more susceptible to oxidation. The equivalent positions in pyrene are 4, 5, 9 and 10 so that the high level of preserved aliphatic H for **9** can be understood in a similar way.

Quantification of the extent of preserved alkyl chain provides a key indicator of catalyst efficacy, but it is still important to positively identify the reaction products. We have used a combination of analytical techniques to suggest the most likely dominant product species in these oxidation reactions. Fig. S8 (ESI $^\dagger$ ) gives the IR spectrum for the product mixture from the organic layer following 2-octadecylpyrene (**9**) oxidation. This shows broad bands at  $1698.5\text{ cm}^{-1}$  and  $1735.6\text{ cm}^{-1}$ , characteristic of the C=O stretching modes associated with saturated non-aromatic aldehydes and aromatic carboxylic acids, respectively. Additionally, the broad peak observed in the -OH region suggests the presence of alcohol or carboxylic acid groups. MS analysis identified a product with  $m/z = 581.31$ , with a suggested formula of  $\text{C}_{34}\text{H}_{45}\text{O}_8$ , (Fig. S9, ESI $^\dagger$ ). In pyrene we have noted that the positions 4, 5, 9 and 10 are the most easily oxidised C=C bonds, so that a likely candidate for this oxidation product is 4-octadecylbiphenyl-2,2',6,6'-tetracarboxylic acid (**10**). Fig. S1 (ESI $^\dagger$ ) shows the  $^1\text{H}$  NMR spectra of **9** and that of the oxidation product mixture. Regarding protons in position  $\alpha$  to the aromatic ring; oxidation of the  $\alpha$ -C-H bond to give C=O is a known reaction and would reduce the intensity of the 3.20 ppm resonance (marked A in Fig. S1, ESI $^\dagger$ ). A new resonance would also be expected between 2.90–3.00 ppm, for the C-H protons in the aliphatic chain that become  $\alpha$  to the ketone group and  $\beta$  to the aromatic ring. Some new features are seen in the  $^1\text{H}$  NMR spectrum of reaction products but these could also be caused by changes in the chemical shifts of protons  $\alpha$  to the aromatic ring system due to oxidation of aromatic carbon. To clarify the situation, Heteronuclear Multiple Bond Correlation (HMBC) 2D NMR spectroscopy was used, which allows the correlation of chemical shifts of two types of nuclei separated from each other by two or more chemical bonds. Using this technique it was possible to observe aromatic protons which were correlated to C from the C=O region, even when those carbons did not give visible signals during standard  $^{13}\text{C}$  NMR analysis. Fig. 1 shows the HMBC 2D spectra with features correlating the C=O region, of the  $^{13}\text{C}$  NMR spectrum with the aromatic protons (C-H) marked confirming that oxidation takes place in the aromatic region of the substrate away from the alkyl substituent, as would be expected for the proposed main product, **10**.



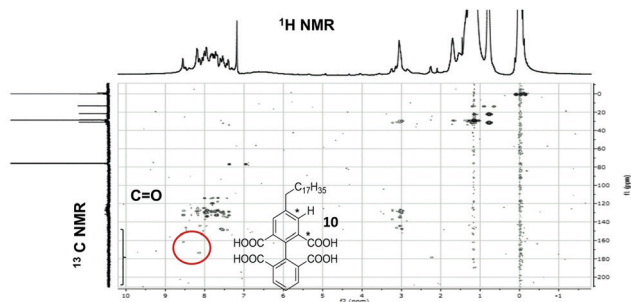
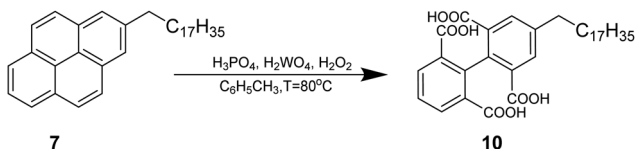


Fig. 1 HMBC (500 MHz,  $\text{CDCl}_3$ ) spectrum of 2-octadecylpyrene oxidation products (organic layer). The structure of the main product 2-octadecylbiphenyl-2,2',6,6'-tetracarboxylic acid, and the correlating elements circled in the spectra, are marked by an \* in the chemical structure.

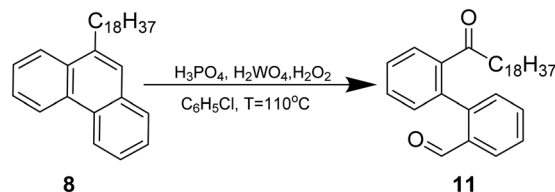
The combined evidence from IR, MS,  $^1\text{H}$  NMR and HMBC shows that the major product of 2-octadecylpyrene oxidation has a preserved aliphatic chain. The product contains four carboxylic acid groups and this, coupled with the knowledge of the regioselectivity preference for oxidation of pyrene, strongly suggests that 4-octadecylbiphenyl-2,2',6,6'-tetracarboxylic acid (**10**) is the major product (Scheme 1). Even without specific product assignment, these observations confirm that the  $\text{H}_2\text{WO}_4/\text{H}_2\text{O}_2$  system delivers the desired reaction selectivity, of ring opening and reducing aromaticity while preserving aliphatic carbon side chains.

For phenanthrene positions 9 and 10 (Fig. S7, ESI<sup>+</sup>) are the most susceptible to oxidation.<sup>11</sup> In the case of 2-octadecylpyrene, (**7**) the corresponding positions (4, 5, 9 and 10) were not hindered by the substituent, and the aromatic region of the molecule was readily oxidized with a high conversion of the substrate (95%, Table 1) with 93% of the products retaining the aliphatic substituent intact. When the alkyl substituent is at a position that favours aromatic oxidation, such as the 9 position of 9-octadecylphenanthrene, (**8**),  $^1\text{H}$  NMR quantification analysis suggests that only 40% of molecules in the post reaction mixture had a preserved alkyl chain. However, only 46% of **8** was converted, so the amount of preserved alkyl chain in the oxidised products will be masked by unreacted substrate. Fig. S10 (ESI<sup>+</sup>) shows the MS spectrum for the reaction mixture after oxidation of **8**. This confirmed a signal at  $m/z = 430.32$  corresponding to unreacted substrate, **8**, and two strong peaks at higher  $m/z$  values consistent with the addition of one oxygen atom ( $m/z = 446.36$ ) and two oxygen atoms ( $m/z = 462.34$ ). The second peak corresponds to 2-nonadecanoylbiphenyl-2-carbaldehyde (**11**) (Scheme 2), as an oxidation product. As further support for this assignment  $^1\text{H}$  NMR spectroscopy confirmed the presence of the aldehyde group (9.75 ppm, Fig. S11, ESI<sup>+</sup>).

The likely presence of (**11**) suggests that the aromatic  $\text{C}=\text{C}$  bond was cleaved by oxidation at the C9–C10 bond position



Scheme 1 2-Octadecylpyrene and its major oxidation product.



Scheme 2 9-Octadecylphenanthrene and a possible product of oxidation consistent with MS analysis.

with high selectivity, so that the aromatic–aliphatic C–C bond was preserved with a ketone formed at the new  $\alpha$ -carbon position. These data provide new insight into the selectivity achievable using the  $\text{H}_2\text{WO}_4/\text{H}_2\text{O}_2$  oxidation system and demonstrates that the chemistry is potentially useful for upgrading of polyaromatic residuals with minimal loss of carbon.

### 3.3. Kinetic studies

The oxidation reactions were also monitored as a function of time to compare the oxidation rates of molecules possessing different numbers of aromatic rings, and varying lengths of alkyl chain. Previously, using RICO chemistry, we found that the number of aromatic rings in a substituted PAH determines the reaction rate, with larger aromatic systems reacting faster than smaller ones.<sup>13</sup> In the case of the tungsten/peroxide catalyst system, when naphthalene, (**12**), phenanthrene, (**13**), and pyrene, (**14**), were used as substrates, it was also found that the reaction rate increased with the increasing number of fused aromatic rings (Fig. 2). This observation means that aromaticity in higher molecular weight polyaromatics can be reduced preferentially in the presence of lower molecular weight ones.

Experiments to determine the competitive rates of oxidation of alkylated aromatics, using 1-decyl naphthalene (**15**), 2-nonylphenanthrene (**7**) and 2-octadecylpyrene (**9**) were also performed (Fig. 3). The difference in reaction rate between 1-decyl naphthalene and 2-nonylphenanthrene was small but it is clear that the phenanthrene derivative reacts faster than the substituted naphthalene

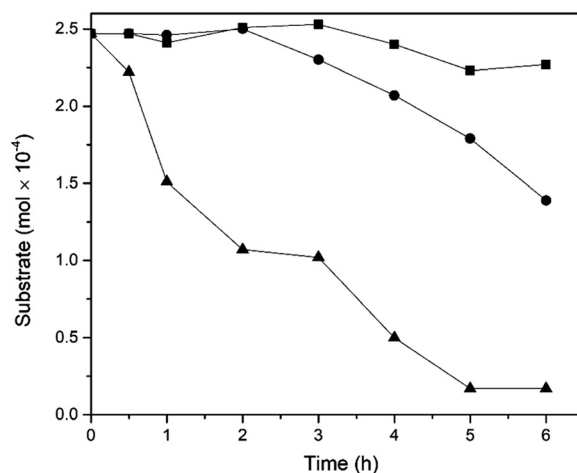


Fig. 2 Comparison of amount of substrate remaining as a function of time for polyaromatic hydrocarbons during competitive reaction between naphthalene (■), phenanthrene (●) and pyrene (▲).



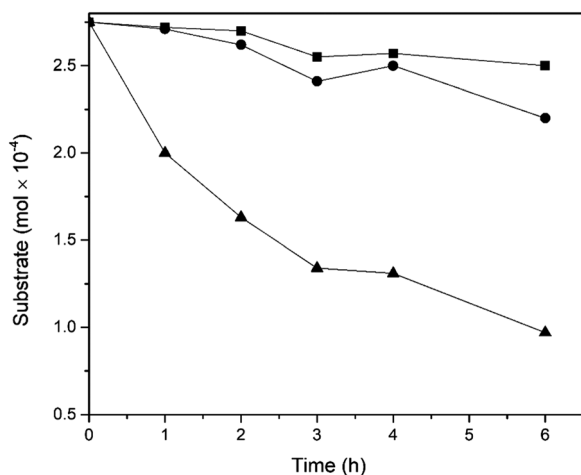


Fig. 3 Comparison of oxidation rates for the competitive reaction between 1-decylanthalene (■), 2-nonylphenanthrene (●), and 2-octadecylpyrene (▲).

example. The difference in alkyl chain length is only one methylene group, so the alkyl chain length would not be expected to be a controlling factor. Moreover, 2-octadecylpyrene was oxidized at a higher rate than other substrates, confirming that the number of fused rings is the key factor determining the rate of oxidation. The same trend was observed when RICO chemistry was used in oxidation of alkylated PAHs.<sup>13</sup> This shows that the  $H_2WO_4/H_2O_2$  catalytic system, similarly to RICO, possesses the ability to selectively reduce the aromaticity, it is also a more attractive approach due to the lower cost of both catalyst and oxidant.

## 4. Conclusions

The results presented clearly indicate that the  $H_2WO_4/H_2O_2$  catalyst system is promising for the selective oxidation of polynuclear aromatic hydrocarbons to reduce aromaticity. It has been shown that the selectivity of oxidation can be tuned by changing the solvent employed in the reaction. Acetonitrile was the best solvent tested in terms of the selectivity for oxidation of the aromatic over the aliphatic region of 2-ethylnaphthalene. This monophasic reaction resulted in the preservation of the alkyl substituent, while reducing the aromatic content. In the homogeneous solvent phase, aromatic oxidation appears more favoured and ring opening to acids can be achieved. For PAHs containing more fused rings the use of acetonitrile is not practical, and a biphasic system, with a less polar organic solvent is required to solubilise the PAH compounds. In these cases, it is still possible to oxidise aromatic regions of the molecules without affecting the alkyl side chains. The aliphatic side chain does not significantly affect the rate of the reaction, but the position of substitution on the aromatic core has an affect on both conversion and degree of oxidation at the  $\alpha$ -carbon position of the alkyl side groups. The relative reaction rates for molecules with different numbers of fused rings was also established, with larger ring systems oxidised at a higher rate than molecules with smaller ones. In general, the  $H_2WO_4/H_2O_2$

oxidation system can be considered to have demonstrated promising chemistry with respect to valorisation of crude oil residues. Judicious choice of solvent gives an oxidation system capable of achieving the required activity and selectivity to produce higher value products with only minor loss of carbon.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors would like to acknowledge research funding from ExxonMobil.

## References

- M. S. Rana, V. Sámano, J. Ancheyta and J. A. I. Diaz, *Fuel*, 2007, **86**, 1216–1231.
- J. G. Speight, *The Chemistry and Technology of Petroleum*, Taylor and Francis Group, 4th edn, 2006.
- S. A. Treese, P. R. Pujado and D. S. J. Jones, *Handbook of Petroleum Processing*, Springer International Publishing, 2nd edn, 2015.
- A. N. Sawarkar, A. B. Pandit, S. D. Samant and J. B. Joshi, *Can. J. Chem. Eng.*, 2007, **85**, 1–24.
- C. Leyva, M. S. Rana, F. Trejo and J. Ancheyta, *Ind. Eng. Chem. Res.*, 2007, **46**, 7448–7466.
- C. Djerassi and R. R. Engle, *J. Am. Chem. Soc.*, 1953, **75**, 3838–3840.
- F. Shi, M. K. Tse and M. Beller, *Adv. Synth. Catal.*, 2007, **349**, 303–308.
- J. Hu, D. Zhang and F. W. Harris, *J. Org. Chem.*, 2005, **70**, 707–708.
- J. W. Cook and R. Schoental, *J. Chem. Soc.*, 1948, 170–173.
- A. Mehra, Y. Wang, J. E. Krechmer, A. Lambe, F. Majluf, M. A. Morris, M. Priestley, T. J. Bannan, D. J. Bryant, K. L. Pereira, J. F. Hamilton, A. R. Rickard, M. J. Newland, H. Stark, P. Croteau, J. T. Jayne, D. R. Worsnop, M. R. Canagaratna, L. Wang and H. Coe, *Atmos. Chem. Phys.*, 2020, **20**, 9783–9803.
- E. Nowicka, M. Sankar, R. L. Jenkins, D. W. Knight, D. J. Willock, G. J. Hutchings, M. Francisco and S. H. Taylor, *Chem. – Eur. J.*, 2015, **21**, 4285–4293.
- B. Plietker, *Synthesis*, 2005, 2453–2472.
- E. Nowicka, T. J. Clarke, M. Sankar, R. L. Jenkins, D. W. Knight, S. Golunski, G. J. Hutchings, D. J. Willock, M. Francisco and S. H. Taylor, *Chem. – Eur. J.*, 2018, **24**, 655–662.
- E. Nowicka, N. W. Hickey, M. Sankar, R. L. Jenkins, D. W. Knight, D. J. Willock, G. J. Hutchings, M. Francisco and S. H. Taylor, *Chem. – Eur. J.*, 2018, **24**, 12359–12369.
- G. B. Payne and P. H. Williams, *J. Org. Chem.*, 1959, **24**, 54–55.
- C. Venturello, E. Alneri and M. Ricci, *J. Org. Chem.*, 1983, **48**, 3831–3833.
- Y. Ishii and Y. Sakata, *Dioxygen Activation and Homogeneous Catalytic Oxidation*, Elsevier Science Publishers B. V., 1991, pp. 411–416.



- 18 S. E. Jacobson, D. A. Muccigrosso and F. Mares, *J. Org. Chem.*, 1979, **44**, 921–924.
- 19 K. Sato, M. Hyodo, J. Takagi, M. Aoki and R. Noyori, *Tetrahedron Lett.*, 2000, **41**, 1439–1442.
- 20 Y. Saito, S. Araki, Y. Sugita and N. Kurata, *US Pat.*, 4831189, 1989.
- 21 D. C. Duncan, R. C. Chambers, E. Hecht and C. L. Hill, *J. Am. Chem. Soc.*, 1995, **117**, 681–691.
- 22 A. C. Estrada, M. M. Q. Simões, I. C. M. S. Santos, M. G. P. M. S. Neves, J. A. S. Cavaleiro and A. M. V. Cavaleiro, *Chem-CatChem*, 2011, **3**, 771–779.
- 23 R. Tayebee, *J. Korean Chem. Soc.*, 2008, **52**, 23–29.
- 24 E. R. R. Young and R. L. Funk, *J. Org. Chem.*, 1998, **63**, 9995–9996.
- 25 G. B. Payne and C. W. Smith, *J. Org. Chem.*, 1957, **22**, 1682–1685.
- 26 L. Barrio, M. Campos-Martin and L. G. Fierro, *J. Phys. Chem. A*, 2007, **111**, 2166–2171.
- 27 I. M. Smallwood, *Handbook of Organic Solvent Properties*, Butterworth-Heinemann, Oxford, 1996.
- 28 P. H. J. Carlsen, T. Katsuki, V. S. Martin and K. B. Sharpless, *J. Org. Chem.*, 1981, **46**, 3936–3938.
- 29 K. Sato, M. Aoki, M. Ogawa, T. Hashimoto and R. Noyori, *J. Org. Chem.*, 1996, **61**, 8310–8311.
- 30 R. Noyori, M. Aoki and K. Sato, *Chem. Commun.*, 2003, 1977–1986.
- 31 Z. Jing, S. Rodrigues, E. Strounina, M. Li, B. Wood, J. R. Underschultz, J. S. Esterle and K. M. Steel, *Int. J. Coal Geol.*, 2019, **201**, 1–13.

