

This is an Open Access document downloaded from ORCA, Cardiff University's institutional repository: <https://orca.cardiff.ac.uk/id/eprint/153486/>

This is the author's version of a work that was submitted to / accepted for publication.

Citation for final published version:

Edwards, Peter P., Pyper, Nicholas C., Jie, Xiangyu, Slocombe, Daniel R. , Catlow, C. Richard A. , Islam, M. Saiful and Dobson, Peter J. 2023. Orbital-selective hole and hole-pair formation and Bose condensation in high-temperature superconductors. *Journal of Solid State Chemistry* 317 (Part A) , 123529. 10.1016/j.jssc.2022.123529

Publishers page: <http://dx.doi.org/10.1016/j.jssc.2022.123529>

Please note:

Changes made as a result of publishing processes such as copy-editing, formatting and page numbers may not be reflected in this version. For the definitive version of this publication, please refer to the published source. You are advised to consult the publisher's version if you wish to cite this paper.

This version is being made available in accordance with publisher policies. See <http://orca.cf.ac.uk/policies.html> for usage policies. Copyright and moral rights for publications made available in ORCA are retained by the copyright holders.



# Orbital-selective hole and hole-pair formation and Bose Condensation in high-temperature superconductors

Peter P. Edwards<sup>1, 2</sup>, Nick Pyper<sup>3</sup>, Xiangyu Jie<sup>2, 4</sup>, Daniel R. Slocombe<sup>5</sup>, Richard Catlow<sup>6</sup>, Saiful Islam<sup>7</sup>

1. OXCCU Tech Ltd, CIE Centre Begbroke Science Park, Oxford OX5 1PF, UK.
2. Inorganic Chemistry Laboratory, Department of Chemistry, University of Oxford, South Parks Road, Oxford OX1 3QR, UK.
3. Department of Chemistry, University of Cambridge, Lensfield Road, Cambridge CB2 1EW, UK.
4. Merton College, University of Oxford, Merton Street, Oxford OX1 4JD, UK.
5. School of Engineering, Cardiff University, Queen's Buildings, The Parade, Cardiff, CF24 3AA, UK.
6. Department of Chemistry, UCL, 20 Gordon Street, London WC1E 6BT, UK.
7. Department of Materials, University of Oxford, Parks Road, Oxford OX1 3PH, UK.

## Abstract

Miguel Alario-Franco is recognised not only for his seminal experimental advances in the field of High  $T_c$  superconductivity but also for his incisive observations on the advances – and the challenges - in the field. In 1995, he highlighted the need for "a new theme" to unite the chemistry and the physics of this spectacular natural phenomenon following the advance by Bednorz and Muller, that surely ranking as one of the greatest-ever discoveries in science.

We review the remarkable recent advances that showed hole (and electron) pairing in the cuprates is found at temperatures above  $T_c$ . Hole-pairing above  $T_c$  was first proposed over 3 decades ago by Mott and Alexandrov. We highlight that the pairing itself will be 'orbital -selective'; holes of predominantly one specific orbital character bind to form the Cooper pairs which then yield the High  $T_c$  state.



Here, a collection of friends and colleagues of Miguel from the disciplines of chemistry, physics, and electronic engineering outline how this as a working, chemically intuitive model in the search for other High  $T_c$  materials.

## Prologue

Miguel has noted that dedicated solid state chemists will always continue their search for other (hopefully, better) High  $T_c$  superconductors even in the absence of any universally-accepted theory of the phenomenon but guided as Roald Hoffmann noted - by "chemical intuition" in its most powerful form [1]. In 1995, in an insightful essay, our 'Birthday Colleague' presented an important overview [2] of the advances made in the eight years that had elapsed since Bednorz and Muller's epoch-making discovery of High Temperature Superconductivity (HTS) in the layered cuprates [3] With that discovery, there was real hope and anticipation for the emergence of an accepted theory for this spectacular phenomenon and the discovery of new classes of materials superconducting at temperatures above liquid nitrogen. Unfortunately, no such universally accepted theory has emerged.


Miguel's assessment was that "Chemical ingenuity, once again, has greatly improved the HTS materials". Hopefully, an example from our own work [4, 5] of such an improvement through the 'Chemical control of HTS', might be taken as a positive reflection of such advances (Figure 1).

## Metal - Superconductor - Insulator Transition

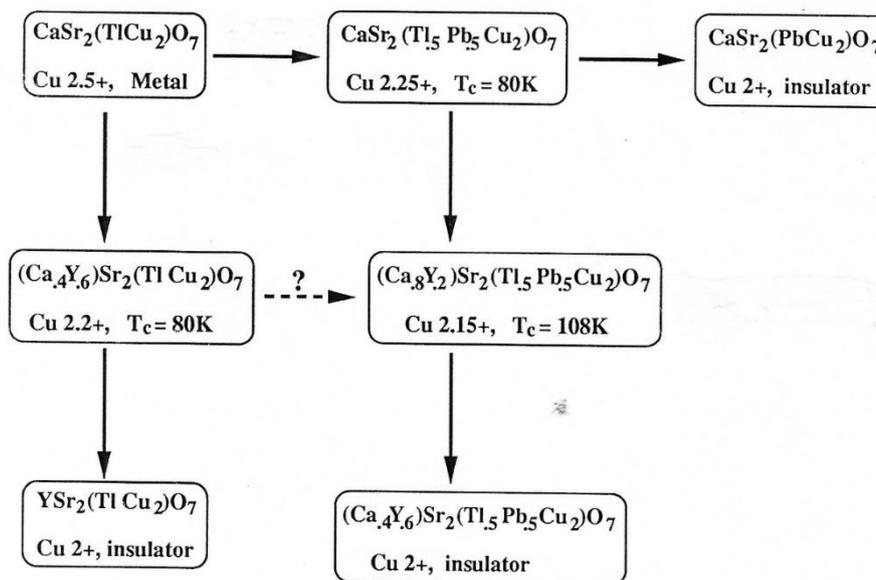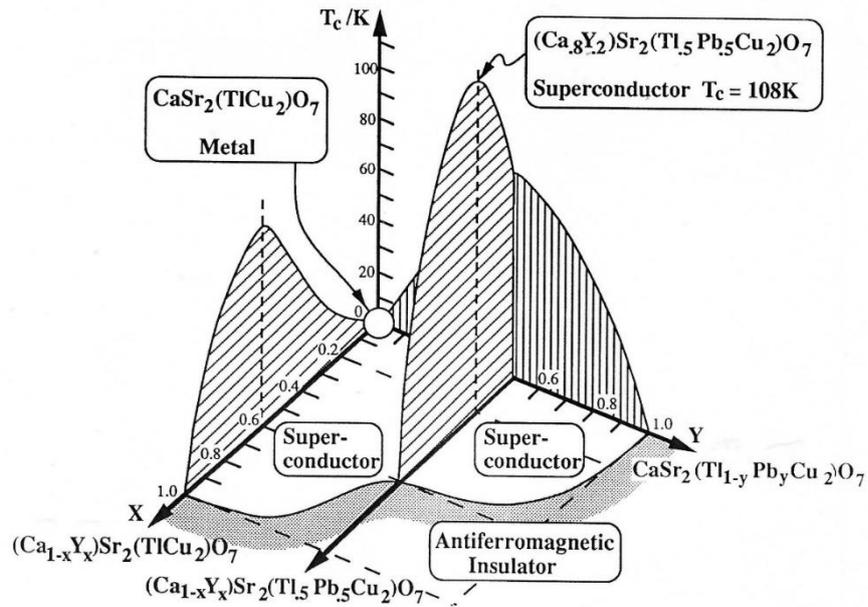

**Figure 1. The chemical control of High Temperature Superconductivity in the septenary cuprates [4]; illustrated from the original data by W Y Liang ( Cambridge University )**

The cuprates are the only materials at room pressure that have superconducting transition temperatures,  $T_c$ , well above the boiling point of liquid nitrogen [6]. However, whilst there are a large number of chemical variants, as exemplified in the septenary cuprates, once the materials are discovered, the chemical control of HTS is powerful and extant. Importantly, the cuprate superconductors all derive from a common, characteristic layered structure made up of one or more  $\text{CuO}_2$  planes with intervening charge reservoirs (Figure 2).

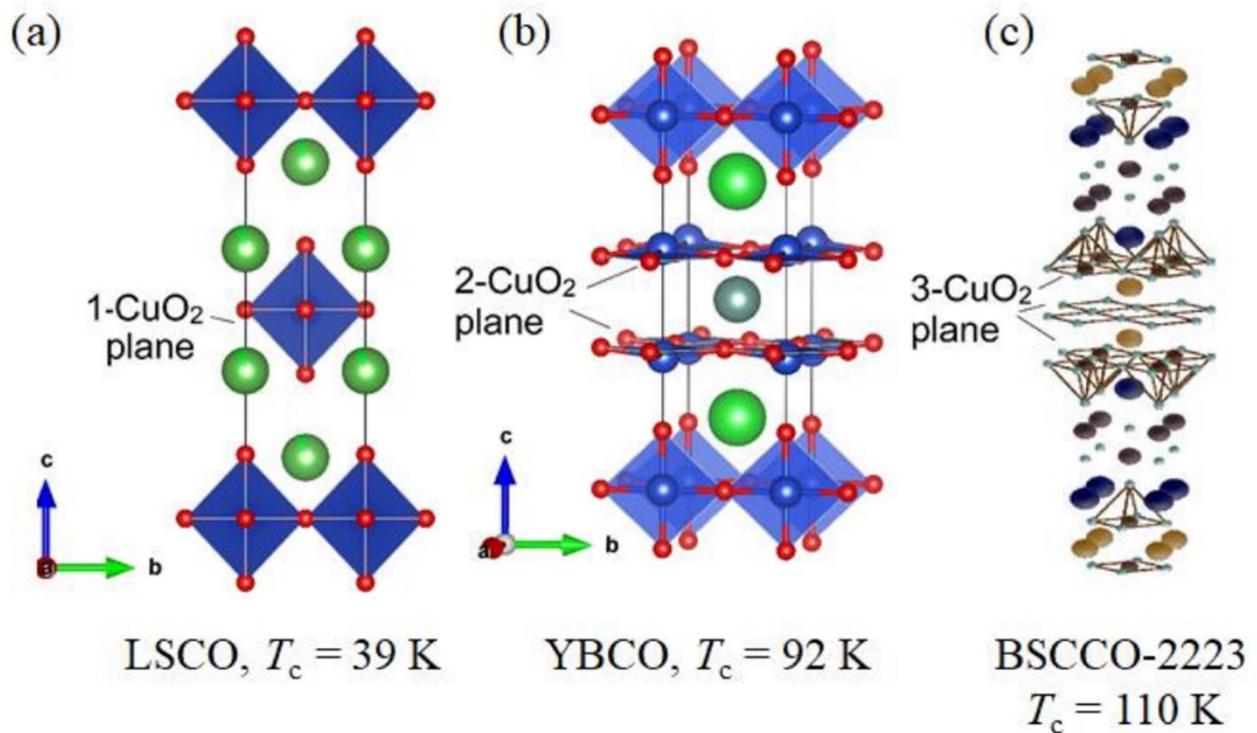

**Figure 2. The crystal structures of the High Temperature Superconducting Cuprate family. [7]**

Miguel correctly argued that in both structural and compositional terms, despite impressive advances in HTS in the layered cuprates, we have - adopting a musical paraphrase - simply been relying upon "...variations on an original theme"[2]. Thus, the vast majority of materials have superconductivity residing in  $\text{CuO}_2$  layers supported by a perovskite skeleton, and supplied with excess holes or electrons by the intervening charge reservoir layers

With that in mind, Miguel concluded - with a characteristic incisive and almost plaintive statement - "Yet, if a new theme could be found..."

This, then, is Miguel's potent challenge for us all ... that of ... "finding a new theme" in understanding HTS and helping to look for other such materials across the Periodic Table. After 35+ years of intense effort, a universally-accepted microscopic theory of HTS is still not established, and that is clearly hampering further progress. It appears, for example, that the cuprate and iron-based superconductors are not amenable to standard ab-initio tools due to strong electron correlations and their proximity to magnetism.

Whilst being conscious of the strong assertion by P.W. Anderson [8] that "...The consensus [*on an accepted theory of High  $T_c$* ] is that there is absolutely no consensus "we attempt to present here a brief overview of recent important developments which may provide a new theme or new themes for a mechanism for HTS, leading to the discovery of other superconducting materials with, potentially, even higher transition temperatures.


We focus on the microscopic origins of the critical hole - formation and hole-pairing mechanism of Cooper pair formation in the cuprates and iron-based superconductors in terms of a highly specific orbital-selective hole formation and hole-pairing. We then discuss the ensuing composition-induced insulator-to-strange- metal transition and, finally, the vexing question of the striking rarity of High  $T_c$  in materials across the Periodic Table.

**Cooper pairs and the insulator-to-strange metal transition in the layered cuprates**

The phenomenon – and explanation – of HTS in the cuprates must surely be embedded in the chemistry and physics of the copper-oxygen layers, suitably 'tuned' either by chemical (substitutional) doping or through auto-injection of charge into the  $\text{CuO}_2$  layers (Figure 2).

Most notable of all developments since Miguel's essay has surely been the widespread realisation *and* identification in the HTS cuprates of the existence of preformed pairs of charge carriers – Cooper pairs – *existing above  $T_c$* , not only giving rise to HTS but also a 'strange metallic state' in the normal state itself [9-12]. In conventional superconductors, Cooper pairs are assumed to form *only at  $T_c$* , where macroscopic coherence of the pairs occurs and superconductivity sets in. In contrast, for the cuprates, it is now acknowledged that Cooper pairs form well above  $T_c$  and become coherently mobile and condense to the superconducting state when the material is cooled to the critical superconducting temperature.


One can readily see as to why the growing appellation of 'strange metals' [13, 14] is so readily applied to the cuprates at  $T > T_c$  by looking at a generic material-sorting - map (Figure 3) involving the electron (hole) densities and electron (hole) mobilities of three prototypical cuprate materials in their normal state as compared to other conducting oxides as well as 'Good' and 'Bad' elemental metals (non-superconducting and superconducting metals, respectively),

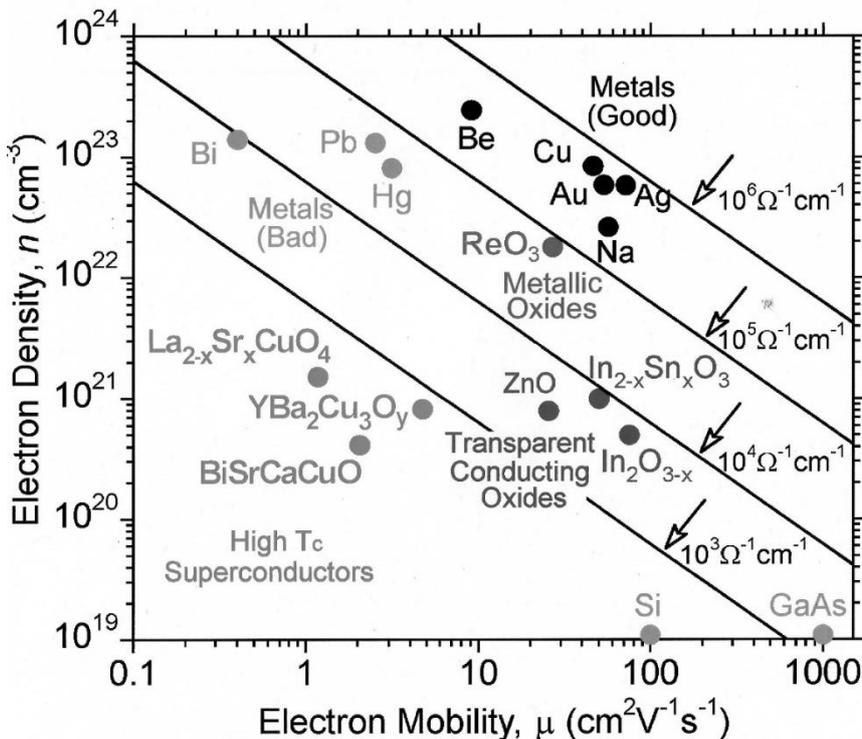

**Figure 3. A Materials Sorting Map (modified from [15]) to include High T<sub>c</sub> Superconductors. Modifications courtesy of Dr V. L Kuznetsov (Oxford University)**

The consensus now emerging is that even in the normal state of HTS cuprates, Cooper pairs, or bipolarons, acting as bosons, are the carriers of electrical charge, unlike conventional metals where single electrons fulfil that role. In these cuprate materials – and potentially other superconducting materials – we see the emergence of a new type of 'strange metal' in which in their normal states, a significant fraction of the electrical current is carried by mobile electron pairs [10, 13, 14, 16, 17]. Indeed, that scenario was first advanced in the 1990's by Mott and Alexandrov [18-22] and elaborated upon by Edwards, Mott and Alexandrov [23].

A recognised and common feature is that the HTS cuprates are strongly correlated electron systems and magnetism and superconductivity either co-exist or are nearby in their phase diagram (Figure 4).

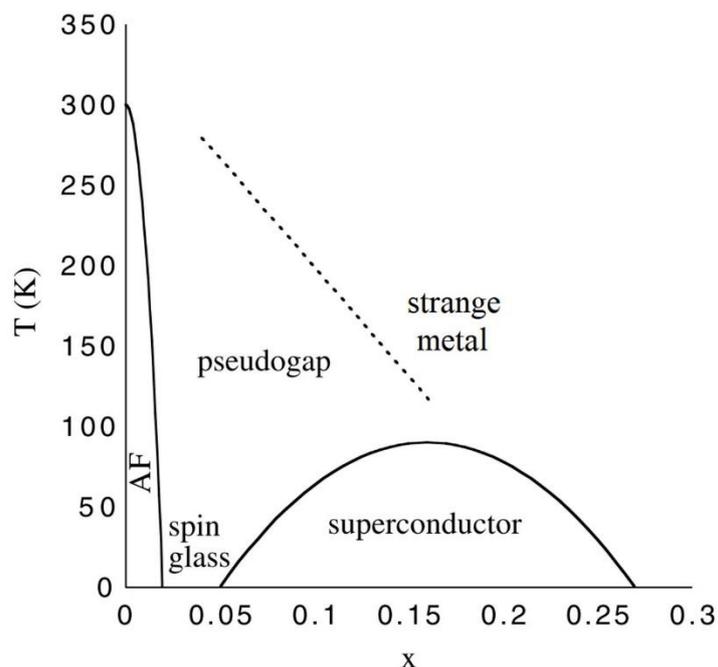

**Figure 4. Schematic phase diagram for the layered High Tc cuprates (modified from ref. [24])**

This observation has been taken as a strong indication that spin fluctuations are a key ingredient in the mechanism for superconductivity. HTS in the cuprates emerges from magnetism upon hole doping of the parent antiferromagnet,  $\text{La}_2\text{CuO}_4$ . The existence of a 'parent' Mott insulator, e.g. in the prototypical cuprate,  $\text{La}_2\text{CuO}_4$ , being a spin 1/2 antiferromagnet, has led to the generally-accepted view that the high  $T_c$  cuprate superconductors can be viewed as a class of doped semiconductors with electronic properties on the insulating side of any transition to the metallic and/ or superconducting state, being qualitatively similar to that in conventional semiconductors.

At zero hole -doping, particles are localised by strong Coulomb repulsions (the Hubbard  $U$ ) and order antiferromagnetically (**Figure 4**). By substituting trivalent La for divalent Sr in  $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ ,  $x$  "excess" holes are added to the two-dimensional  $\text{CuO}_2$  layer with their concentration dictated by the compositional parameter,  $x$ . Thus, the composition-dependent, in-plane  $\text{CuO}_2$  electronic structure and properties are dominated by holes, introduced randomly by chemical doping (e.g. substitution of  $\text{Sr}_{2+}$  for  $\text{La}_{3+}$  in  $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ ). Such structural and electronic disorder gives rise to a mobility edge in the electronic density of states in this 2D system

With increasing  $x$ , as holes are continuously added, the low temperature antiferromagnetism (AFM) disappears and – ultimately- an unconventional, strange metallic state emerges in the normal state and High  $T_c$  at lower temperatures. Many authors have proposed that this characteristic magnetic behaviour – strong antiferromagnetism within the 2D  $\text{CuO}_2$  planes (Figure 2) being modified by added holes - might provide the gateway to HTS. Here, the magnetic 'glue' responsible for hole-Cooper pairing and HTS coming from dynamic spin fluctuations associated with proximity to an antiferromagnetic state.

Jarrell *et al.* and others [25, 26], early on, outlined a phenomenological model for the composition-induced insulator-metal transition in the cuprates in which the electronic conduction is shown to be predominantly intralayer, i.e. confined to the Cu-O layers. In the parent compound  $\text{La}_2\text{CuO}_4$ ,


the formal valence of Cu is 2+, which means its electronic configuration is  $d^9$ . The local crystal symmetry splits the constituent, e.g. orbitals, so that the highest partially occupied d-orbital has the character  $d_{x^2-y^2}$  (Supplementary Information).

At low doping (substitutional) levels, the excess hole (acceptor) states occupies a two-dimensional hydrogenic orbital in the  $\text{CuO}_2$  plane. The oxygen holes are at first localised/coulombically bound to their accompanying (parent) dopant ion (e.g.  $\text{Sr}^{2+}$ ) and have a characteristic Bohr radius of between  $8 \pm 2 \text{ \AA}$  in the  $\text{CuO}_2$  plane, typically encompassing 1-2 unit cells. The temperature dependence of the electrical resistivity in the insulating regime in the cuprates has been attributed to variable-range hole hopping of excess charge carriers between Anderson- localised states [25, 26].

At higher values of  $x$ , as charted by Catlow, Islam and co-workers [27-30], we see the natural progression to the formation of bound hole pairs, ( peroxy) bipolarons, also spatially localised at these intermediate values of the compositional parameter  $x$ .

Importantly, hole formation and the subsequent hole- pairing itself appears to be orbital – selective, meaning that excess holes and pairs of holes are formed from specific atomic orbitals of the oxidised  $\text{O}^{2-}$  ion to yield  $\text{O}^-$  and these states ultimately combine to form the Cooper pairs of the superconductor.

Catlow, Islam and co-workers have investigated in detail the atomic/orbital structure and energies of such bipolarons in substitutionally- doped  $\text{La}_2\text{CuO}_4$  [27-30].

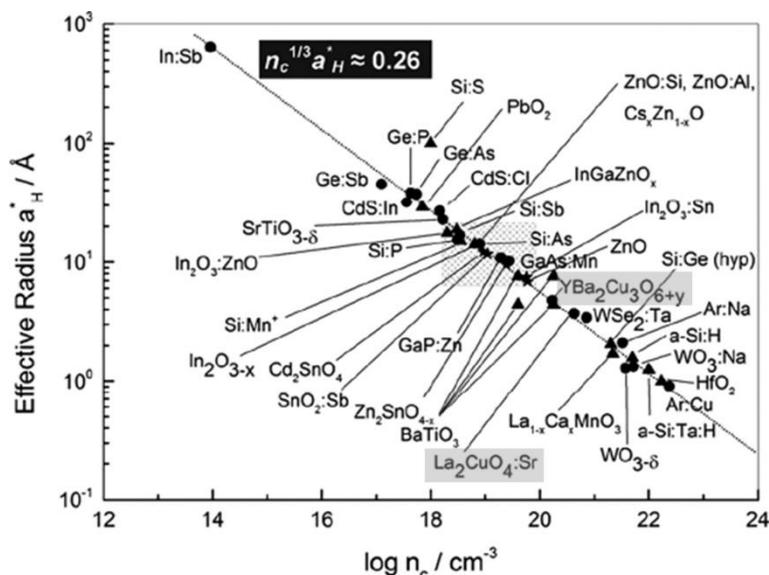

**Figure 5. A plot of the critical carrier density,  $n_c$ , as a function of  $a_H^*$ , the effective Bohr orbit radius of a range of materials ( Ref [31]). The conditions for the metal-insulator transition for two cuprates are shown in grey shading.**

Now, once formed, these charged spin-zero bosons, like ordinary single electron/hole carriers in doped semiconductors, screen the random, localising potential. As noted by Alexandrov and Mott [21] it is expected that the Mott criterion for the insulator-metal transition [32] will be valid also in the case of Bose particles, with  $2n$  instead of  $n$  and  $a_H^* = \dots$  and with  $\epsilon_0 \sim 100$  and  $m^* \sim 10m_e$  this yields a critical density ( $n_c$ ) for the metal-insulator transition of ca.  $10^{21} \text{ cm}^{-3}$  (Figure 5).

The generally-accepted phase diagram in the cuprates shows the consequences of adding "excess holes" to the CuO<sub>2</sub> planes through chemical substitution and the evolution, ultimately, to an anomalous or strange metallic state from a Cooper-pair insulating state separated at the lowest temperature by a Quantum Critical Point, QCP (Figure 4).

Of course, the high- and low - temperature ( $T = 0\text{K}$ ) crossover behaviour from insulator- to – (strange) metal is completely hidden under normal conditions by the existence of the high-temperature superconducting phase.

Applying a high magnetic field to suppress superconductivity enables a detailed study of that electronic transition in the normal state. Boebinger *et al.* [33] were first able to study the basic insulator-metal transition, in the absence of superconductivity, as a function of carrier concentration achieved by using a 61T pulsed magnetic field to suppress superconductivity in La<sub>2-x</sub>Sr<sub>x</sub>CuO<sub>4</sub> single crystals.

The remarkable finding is that the insulator-to-metal crossover transition occurs for compositions near optimum doping. Thus, the low temperature (normal state) insulator- (*now*) strange metal transition, reflected in the modified Mott criterion, where the carriers are bosons rather than fermions, is linked to the carrier concentration at the optimum  $T_c$  of the superconducting phase of the layered cuprate. This reflects the condition for the Bose-Einstein Condensation of the doubly charged, paired-hole carriers, or bipolarons, into the superconducting state of the layered cuprates [23, 34].

Mott first proposed [18, 19] that this non-degenerate gas of bosons carries the current above  $T_c$  and accounts for the abnormal behaviour of this strange metal not shown by conventional BCS-type superconductors in their normal state.

It is also now recognised that when electrons (or holes) form Cooper pairs in a 2D disordered system (such as the cuprates (Figure 2)) the ground state must *either* be a superconductor *or* an insulator with, interestingly, *no intervening, conventional "metallic state"* [23]. This is recognised from the scaling theory of localisation, which predicts that a conventional metallic state is absent at  $T = 0\text{K}$  in such disordered systems because of quantum interference [35, 36].

We now turn to the specific orbital structure at a microscopic level upon the introduction of excess holes in the CuO<sub>2</sub> layers and how they interact to form hole-pair bosons which then carry the supercurrent. We highlight how orbital structure – or orbital selectivity - in the cuprates (and other High  $T_c$  superconductors, e.g. FeSe) may be pivotal to understanding the microscopic origins and interplay of electronic structure and High  $T_c$ . It may also be a natural explanation as to the rarity of High  $T_c$ .

### **The rarity of High $T_c$ : Is a characteristic orbital-selective structure responsible?**

A continuing challenge to any understanding of High  $T_c$  materials is that, despite the huge advances made since 1987, almost as remarkable as HTS itself, is the fact that the layered cuprates remain the only materials at room pressure that have superconducting transition temperatures above the boiling point of liquid nitrogen [3]. Any satisfactory theory of HTS must therefore explain not only its microscopic physical origin, which has been the major focus of attention hitherto, but also the equally-striking rarity of the phenomenon exhibited by only a limited number of classes of materials that have been discovered [37, 38].


It is in the reasoning for, and possible explanation behind, this chemical uniqueness we believe that one might find the... "new theme"... that Miguel so powerfully advocated [2].

Pyper and Edwards [37, 38] pointed out that the rarity of HTS could be naturally explained if a highly specific and characteristic electronic structure is needed for hole formation and subsequent hole pairing and for a material to exhibit such superconductivity. And more recently, the concept of orbital-selective Cooper pairing has been invoked to rationalise metallicity and superconductivity in FeSe and related materials [39, 40]. There, also, the pairing arises from electrons of one specific orbital character which bind to form the Cooper pairs of the superconductor. For FeSe, for example, it is predominantly the  $d_{yz}$  orbitals of Fe atoms that lead to orbital - selective Cooper pairing [39].

In these models, the pairing of holes or electrons is therefore highly dependent upon the specific atomic orbitals that combine to form the Cooper pairs, which ultimately condense at  $T_c$ . As representative, we summarise the basic atomic orbital structure giving rise to both hole- and electron- pairing in the cuprates as well as the oxidised bismuthates (Figure 7).

Thus, in the  $\text{CuO}_2$  sheets, the  $d_{x^2-y^2}$  orbital points directly at the four  $\text{O}_2^-$  ions. (Supplementary Information) All the constituent d orbitals are filled with two electrons except for this  $d_{x^2-y^2}$  orbital which contains one unpaired electron. Both the modelling [27-30] and quantum chemistry [41-45] approaches show that the hole-doping/chemical oxidation of the  $\text{CuO}_2$  sheets brought about by replacement of  $\text{La}_{3+}$  by  $\text{Sr}_{2+}$  ions to (ultimately) produce the High  $T_c$  material proceeds by the removal of an electron from the highest occupied oxygen  $p_y$  orbitals to leave a  $\text{Cu}_{2+} \dots \text{O}^- \dots \text{Cu}_{2+}$  subunit whose singly occupied electronic orbitals are depicted in Figure 7 (a).

Since the  $\text{O}-p_y$  orbital is orthogonal to both the  $\text{Cu}_{2+} d_{x^2-y^2}$  orbitals, both the  $(\text{O}^- \dots \text{Cu}_{2+})$  couplings are ferromagnetic. The direct overlap between a 3d orbital on one  $\text{Cu}_{2+}$  ion with the corresponding 3d orbital on the other  $\text{Cu}_{2+}$  ion is almost certainly too small to account for the magnitude of the (strong) antiferromagnetic coupling between the two  $\text{Cu}_{2+}$  ions. Therefore, this coupling almost certainly arises through a superexchange mechanism involving the filled  $p_x$  and  $p_x$  orbitals on the intervening  $\text{O}_2^-$  ion (Figure 6).

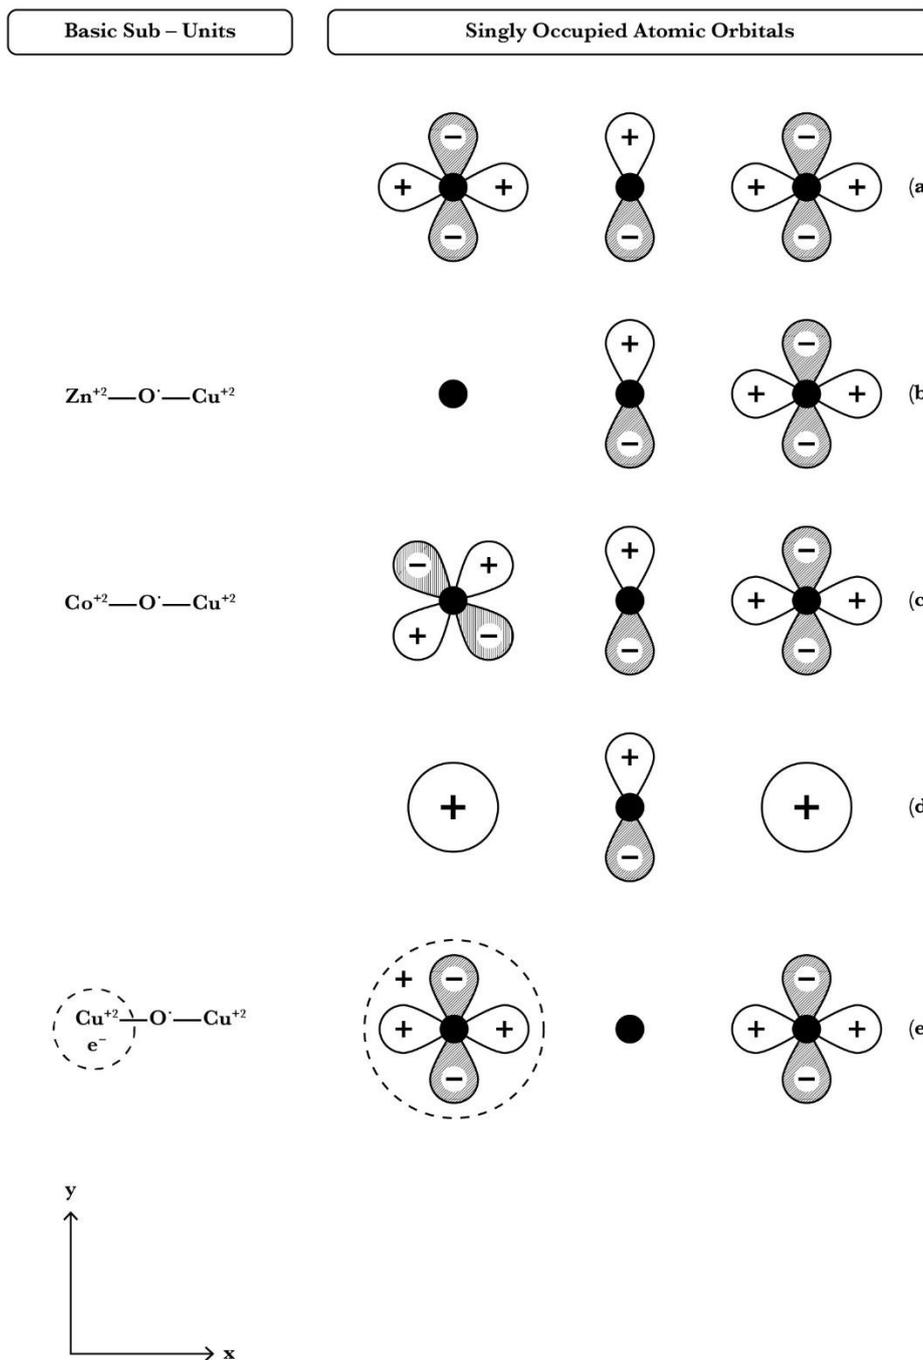

**Figure 6.** The orbital structures of the fundamental electronic entities considered responsible for high-temperature superconductivity (a) and its suppression by chemical dopants (e.g. (b)  $Zn^{2+}$  and (c)  $Co^{2+}$ ) in the layered cuprates. Also shown is the corresponding situation for the oxidised bismuthates (d) and the electron-doped cuprates (e) from Ref [37].

The necessity for specific, orbital-selective electronic entities (or quasiparticles) considered responsible for HTS in the hole-doped cuprates- also explains its suppression through substitution by chemical dopants (eg  $Zn^{2+}$  and  $Co^{2+}$ ) as well as superconductivity in the oxidised bismuthates and the n-type electron-doped reduced cuprates [37, 38].

This orbital – selective picture naturally links into the proxy bipolaron picture outlined by Catlow et al. [27-30] and provides a natural – and highly specific – mechanism by which these current carrying holes are coupled into the Bose pairs that ultimately condense to yield superconductivity [18, 19].

It is important to note that the oxidation of the O<sub>2</sub>-ion in the antiferromagnetically coupled CuO<sub>2</sub> sheets gives rise to characteristic electronic structures that is fundamentally, qualitatively different from those that would be produced if the oxidation were to proceed by ionisation of one of the two Cu<sub>2+</sub> ions to yield Cu<sup>3+</sup>. This, in the former case, one would generate a subunit containing three singly occupied orbitals, whereas in the latter, the resulting subunit contains just one unpaired electron [37].

Of most significance here is the proposal that in both the copper-based and iron-based superconducting materials both hole- and electron - pair formation arises from orbital - selective correlations in the normal state from which HTS emerges.

The view we advance, therefore, is that HTS can arise only in materials containing sub-units having such a highly specific orbital structure at a microscopic level. This provides a natural explanation for the rarity of the HTS phenomena and may assist in developing "rules" for looking for other HTS materials (see following section).

A related line of reasoning has been advanced in by Sprau *et al.*, who invoked orbital-selective Cooper pairing of electrons in FeSe, meaning that electrons of only one specific orbital character, there, the d<sub>yz</sub> orbital of Fe atoms, bind to form the Cooper pairs of the superconductor [39, 40].

There is support that not only the cuprates but also in the strikingly similar family of unconventional superconductors T<sub>c</sub> can be shown to scale with the strength of the interaction, J, between nearest - neighbour local moments in their parent antiferromagnetic states. One model has T<sub>c</sub> as a product of the strength of this antiferromagnetic coupling as well as the strength of the ferromagnetic coupling [37, 38, 41-45]. Further work is needed in that particular area, building upon the idea of estimating the value of T<sub>c</sub>.

### **A suggested strategy: "A new way of thinking [2]"?**

The view we advance is that HTS can only arise in materials containing sub-units of the type noted earlier, having a very special and characteristic electronic structure. On that basis, and thinking primarily of the chemical elements in the d-block of the Periodic Table, our strategy for searching for new families of superconductors can therefore be outlined:

- Search for 2D or nearly - 2D AFM materials that contain local moments whose cation - cation AFM interactions arise from strong superexchange mediated by an intervening anion. Ideally, these next-nearest neighbour AFM magnetic interactions, *occurring between effective spin ½ constituents*, are at least comparable to, but preferably larger than, that found in the cuprates. As noted by DiSalvo [45] this represents a large cation-anion mixing of the wavefunction at the Fermi level. We highlight a major- and critical - focus is that the metal cations comprising the critical sub-units each have an effective spin  $S = \frac{1}{2}$ .
- Identify classes of these 2D or nearly 2D strongly-antiferromagnetic materials which, upon hole doping will contain those characteristic / fingerprint orbitally-selective units. Such materials will need to be "tuned" by substitutional doping (cation or anion substitution ) to

induce p-type hole conductivity to effect a transition to a strange- metallic state across the Mott critical density (Figure 5).

- Think of the resulting combinations of metal atomic orbitals, in association with an 'oxidised anion' – i.e. placing a hole on the anion- (oxide, nitride, carbide- possibly halide) - that can give rise to the basic sub-units having the hole on the anion residing in an orthogonal p orbital next to the metal  $S=1/2$  orbitals (Figure 6 (a) is for the case of  $\text{Cu}^{2+}$  and an intervening O.- ) This characteristic and highly specific orbital-selective electronic structure is then the necessary precursor for both hole formation and subsequent hole-pairing.
- Realise that the generation of the cation  $S=1/2$  state in the AFM material will depend completely upon the normal chemical oxidation state of the metal and upon its local coordination environment. For d-block cations, their crystal field splitting characteristics, with highly distorted near -neighbour environments, must favour non-degenerate states and the required spin-1/2 configuration. Alternatively, the cation valence necessary to produce the necessary spin-1/2 ion can be adjusted through low- to high- crystal field strengths of the surrounding anions or by moving from 1<sup>st</sup>- to – 2<sup>nd</sup>-to 3<sup>rd</sup> row elements. Changing the crystal field strength of the coordinated anion can be tailored to induce the necessary changes in crystal field splitting and the associate high-or low-spin configuration to produce the effective  $S= \frac{1}{2}$  state required on the metal cation.

## Epilogue

Here, we have highlighted the concept of orbital-selective hole and hole-pair (Cooper pair) formation in the quasi -2D High  $T_c$  cuprates and the iron-based superconductors.

Association of these spinless pairs ultimately yields, through Bose-Einstein Condensation, to a High  $T_c$  superconductor. Importantly, such pairs (bosons) exist above the superconducting critical temperature. This orbital - selective Cooper pair formation – and ultimately superconductivity - can only derive from highly specific and characteristic arrangements of orbitals. This orbital – selective interaction may be pivotal to understanding the microscopic electronic structure of the pairing mechanism in superconducting cuprate and other materials (e.g. FeSe). It would also account for why- so far- there are only a small number of basic types of superconductors currently known above the temperature of liquid nitrogen.


To remind ourselves of Miguel's 1995 commentary ..." experimentalists continue their search (*for other superconductors*) in spite of the lack of a theory and, in this search, imagination, luck, and a combination of both with basic knowledge – something which is often called "chemical intuition" – are usually the commonest tools".

Building on this extant arsenal already in the hands of experimentalists, we hope that our vision of Miguel's "... new theme..." - orbital- selective Cooper pairing to yield bipolarons and their Bose- Einstein Condensation, - may provide the focussed strategy for discovering new classes of materials in which superconductivity emerges at temperatures greater than the highest transition temperature achieved in the cuprate or iron- based superconductors. This is surely one of the major scientific challenges of this century.

---

Supplementary Material

**The crystal-field splitting of the five 3d orbitals characteristic of the high temperature superconducting cuprates**

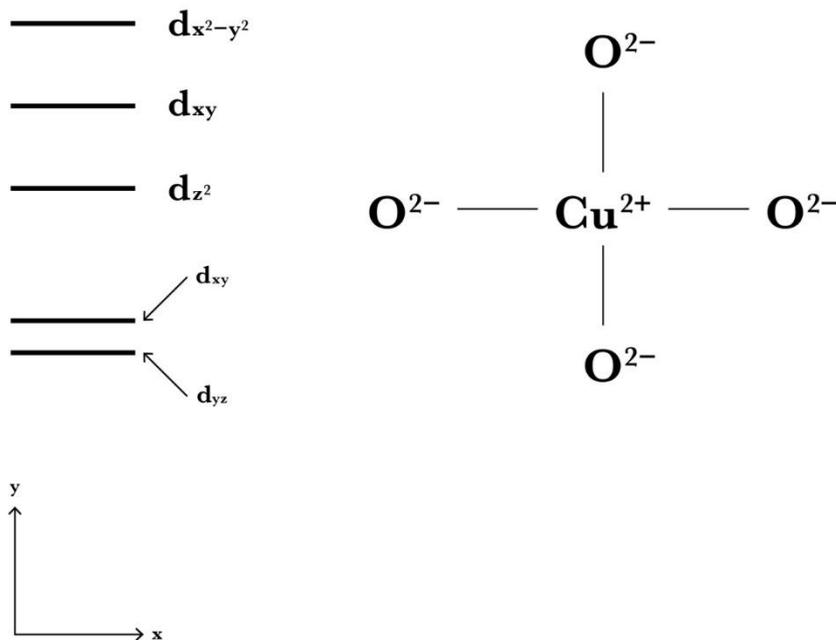

## References:

- [1] R. Hoffmann, Solids and surfaces : a chemist's view of bonding in extended structures, VCH Publishers 1988.
- [2] M.A. Alario-Franco, High temperature superconducting materials, *Advance Materials* 7 (1995) 229-232.
- [3] J.G. Bednorz, K.A. Müller, Possible high  $T_c$  superconductivity in the Ba– La– Cu– O system, *Zeitschrift für Physik B Condensed Matter* 64(2) (1986) 189-193.
- [4] R. Liu, P. P. Edwards, The Chemical Control of High-Temperature Superconductivity; The Metal-Superconductor-Insulator Transition in  $(\text{Tl}_{1-y}\text{Pb}_y) \text{Sr}_2 (\text{Ca}_{1-x}\text{Y}_x) \text{Cu}_2\text{O}_7$ , *Materials Science Forum*, Trans Tech Publ, 1993, pp. 435-464.
- [5] R. Liu, P. P. Edwards, Y. Huang, S. Wu, P. Wu, Superconductivity and the metal-semiconductor transition in the septenary oxide system,  $(\text{Tl}_{0.5}\text{Pb}_{0.5})(\text{Ca}_{1-y}\text{Y}_y) \text{Sr}_2\text{Cu}_2\text{O}_{7-\delta}$ , *Journal of Solid State Chemistry* 86(2) (1990) 334-339.
- [6] K. A. Müller, The unique properties of superconductivity in cuprates, *Journal of Superconductivity and Novel Magnetism* 27(10) (2014) 2163-2179.
- [7] R. Jha, Y. Mizuguchi, Superconductivity in  $\text{La}_2\text{O}_2\text{M}_4\text{S}_6$  -Type Bi-based Compounds: A Review on Element Substitution Effects, *Condensed Matter* 5(2) (2020) 27.
- [8] W. Michael, W.J. Davidson, A dialogue on the theory of high  $T_c$ , *Physics Today* (1991) 55.
- [9] C.J. Humphreys, A two-phase charge-density real-space-pairing model of high- $T_c$  superconductivity, *Acta Crystallographica Section A: Foundations of Crystallography* 55(2) (1999) 228-233.
- [10] H.-B. Yang, J. Rameau, P. Johnson, T. Valla, A. Tsvelik, G. Gu, Emergence of preformed Cooper pairs from the doped Mott insulating state in  $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ , *Nature* 456(7218) (2008) 77-80.
- [11] L. Li, Y. Wang, S. Komiyama, S. Ono, Y. Ando, G. Gu, N. Ong, Diamagnetism and Cooper pairing above  $T_c$  in cuprates, *Physical Review B* 81(5) (2010) 054510.
- [12] P. Zhou, L. Chen, Y. Liu, I. Sochnikov, A.T. Bollinger, M.-G. Han, Y. Zhu, X. He, I. Božović, D. Natelson, Electron pairing in the pseudogap state revealed by shot noise in copper oxide junctions, *Nature* 572(7770) (2019) 493-496.
- [13] C. Yang, H. Liu, Y. Liu, J. Wang, D. Qiu, S. Wang, Y. Wang, Q. He, X. Li, P. Li, Signatures of a strange metal in a bosonic system, *Nature* 601(7892) (2022) 205-210.
- [14] P.W. Phillips, N.E. Hussey, P. Abbamonte, Stranger than metals, *Science* 377(6602) (2022) eabh4273.
- [15] P.P. Edwards, A. Porch, M.O. Jones, D.V. Morgan, R.M. Perks, Basic materials physics of transparent conducting oxides, *Dalton transactions* (19) (2004) 2995-3002.

- [16] I. Božović, J. Levy, Pre-formed Cooper pairs in copper oxides and LaAlO<sub>3</sub>—SrTiO<sub>3</sub> heterostructures, *Nature Physics* 16(7) (2020) 712-717.
- [17] K.M. Bastiaans, D. Chatzopoulos, J.-F. Ge, D. Cho, W.O. Tromp, J.M. van Ruitenbeek, M.H. Fischer, P.J. de Visser, D.J. Thoen, E.F. Driessen, Direct evidence for Cooper pairing without a spectral gap in a disordered superconductor above T<sub>c</sub>, *Science* 374(6567) (2021) 608-611.
- [18] N. F. Mott, High temperature superconductivity; the spin polaron theory, *Contemporary physics* 31(6) (1990) 373-385.
- [19] N. F. Mott, High-temperature superconductors above T<sub>c</sub>, *Physica A: Statistical Mechanics and its Applications* 168(1) (1990) 221-228.
- [20] N.F. Mott, Insulator-metal transitions in high-T<sub>c</sub> superconductors, *Philosophical Magazine Letters* 69(3) (1994) 155-157.
- [21] A. S. Alexandrov, N.F. Mott, *Polarons and Bipolarons*, World Scientific 1996.
- [22] A. S. Alexandrov, N. F. Mott, Do pairs exist above T<sub>c</sub>?, *Superconductor Science and Technology* 6(4) (1993) 215.
- [23] P. P. Edwards, N. F. Mott, A. S. Alexandrov, The insulator-superconductor transformation in cuprates, *Journal of Superconductivity* 11(1) (1998) 151-154.
- [24] M. Norman, C. Pépin, The electronic nature of high temperature cuprate superconductors, *Reports on Progress in Physics* 66(10) (2003) 1547.
- [25] M. Jarrell, D. Cox, C. Jayaprakash, H. Krishnamurthy, Phenomenological model of the magnetic properties of La<sub>2-x</sub>Sr<sub>x</sub>CuO<sub>4-y</sub>, *Physical Review B* 40(13) (1989) 8899.
- [26] C. Chen, R. Birgeneau, M. Kastner, N. Preyer, T. Thio, Frequency and magnetic-field dependence of the dielectric constant and conductivity of La<sub>2</sub>CuO<sub>4+y</sub>, *Physical Review B* 43(1) (1991) 392.
- [27] M. Islam, M. Leslie, S. Tomlinson, C. R. A. Catlow, Computer modelling studies of defects and valence states in La<sub>2</sub>CuO<sub>4</sub>, *Journal of Physics C: Solid State Physics* 21(6) (1988) L109.
- [28] C. R. A. Catlow, S. Tomlinson, M. Islam, M. Leslie, Hole-pairing mechanisms in La<sub>2</sub>CuO<sub>4</sub>, *Journal of Physics C: Solid State Physics* 21(33) (1988) L1085.
- [29] C. R. A. Catlow, M. Islam, X. Zhang, The structure and energies of peroxy bipolarons in, *Journal of Physics: Condensed Matter* 10(3) (1998) L49.
- [30] X. Zhang, C. R. A. Catlow, Elastic and coulombic contributions to real-space hole pairing in doped La<sub>2</sub>CuO<sub>4</sub>, *Journal of Materials Chemistry* 1(2) (1991) 233-238.
- [31] A.T. Vai, V.L. Kuznetsov, H. Jain, D. Slocombe, N. Rashidi, M. Pepper, P.P. Edwards, The Transition to the Metallic State in Polycrystalline n-type Doped ZnO Thin Films, *Z. Anorg. Allg. Chem.* 640(6) (2014) 1054-1062.
- [32] P.P. Edwards, M.J. Sienko, Universality aspects of the metal-nonmetal transition in condensed media, *Physical Review B* 17(6) (1978) 2575.
- [33] G. Boebinger, Y. Ando, A. Passner, T. Kimura, M. Okuya, J. Shimoyama, K. Kishio, K. Tamasaku, N. Ichikawa, S. Uchida, Insulator-to-metal crossover in the normal state of La<sub>2-x</sub>Sr<sub>x</sub>CuO<sub>4</sub> near optimum doping, *Physical Review Letters* 77(27) (1996) 5417.
- [34] A. S. Alexandrov, P. P. Edwards, High-T<sub>c</sub> cuprates: a new electronic state of matter?, *Physica C: Superconductivity* 331(2) (2000) 97-112.
- [35] C. Yang, Y. Liu, Y. Wang, L. Feng, Q. He, J. Sun, Y. Tang, C. Wu, J. Xiong, W. Zhang, Intermediate bosonic metallic state in the superconductor-insulator transition, *Science* 366(6472) (2019) 1505-1509.
- [36] P.W. Phillips, Free at last: Bose metal uncaged, *Science* 366(6472) (2019) 1450-1451.
- [37] N. C. Pyper, P. P. Edwards, The characteristic electronic structure needed for high-temperature superconductivity, *Chemical Physics Letters* 176(2) (1991) 225-232.
- [38] N. C. Pyper, P. P. Edwards, Reply to the Comment on “the characteristic electronic structure needed for high-temperature superconductivity”, *Chemical Physics Letters* 185(3-4) (1991) 409-414.
- [39] P.O. Sprau, A. Kostin, A. Kreisel, A.E. Böhmer, V. Taufour, P.C. Canfield, S. Mukherjee, P.J. Hirschfeld, B.M. Andersen, J.S. Davis, Discovery of orbital-selective Cooper pairing in FeSe, *Science* 357(6346) (2017) 75-80.
- [40] A. Kostin, P.O. Sprau, A. Kreisel, Y.X. Chong, A.E. Böhmer, P.C. Canfield, P.J. Hirschfeld, B.M. Andersen, J. Davis, Imaging orbital-selective quasiparticles in the Hund’s metal state of FeSe, *Nature materials* 17(10) (2018) 869-874.
- [41] Y. Guo, J.-M. Langlois, W.A. Goddard III, Electronic structure and valence-bond band structure of cuprate superconducting materials, *Science* 239(4842) (1988) 896-899.

- [42] G. Chen, W.A. Goddard III, The magnon pairing mechanism of superconductivity in cuprate ceramics, *Science* 239(4842) (1988) 899-902.
- [43] G. Chen, J.-M. Langlois, Y. Guo, W.A. Goddard III, Superconducting properties of copper oxide high-temperature superconductors, *Proceedings of the National Academy of Sciences* 86(10) (1989) 3447-3451.
- [44] R. Nesbet, Spin-flip pairing in CuO<sub>2</sub> superconductors, *Solid state communications* 69(11) (1989) 1103-1106.
- [45] F.J. Disalvo, Synthesis of new classes of high-temperature superconducting materials, *Chemistry of High-Temperature Superconductors*, 1987, pp. 49-55. Editors; David L Nelson, M Stanley Whittingham and Thomas F George, American Chemical Society, Washington, DC 1987.