

Online Research @ Cardiff

This is an Open Access document downloaded from ORCA, Cardiff University's institutional repository: <https://orca.cardiff.ac.uk/id/eprint/138948/>

This is the author's version of a work that was submitted to / accepted for publication.

Citation for final published version:

Yang, Pengfei, Moloney, Mark G., Zhang, Fei and Ji, Wei 2018. Surface hydrophobic modification of polymers with fluorodiazomethanes. *Materials Letters* 210 , pp. 295-297. 10.1016/j.matlet.2017.09.008 file

Publishers page: <http://dx.doi.org/10.1016/j.matlet.2017.09.008>
<<http://dx.doi.org/10.1016/j.matlet.2017.09.008>>

Please note:

Changes made as a result of publishing processes such as copy-editing, formatting and page numbers may not be reflected in this version. For the definitive version of this publication, please refer to the published source. You are advised to consult the publisher's version if you wish to cite this paper.

This version is being made available in accordance with publisher policies.

See

<http://orca.cf.ac.uk/policies.html> for usage policies. Copyright and moral rights for publications made available in ORCA are retained by the copyright holders.



Surface hydrophobic modification of polymers with fluorodiazomethanes

Pengfei Yang^{a,b}, Mark G. Moloney^{a,†}, Fei Zhang^{a,c}, Wei Ji^d

^a Chemistry Research Laboratory, Department of Chemistry, University of Oxford, OX1 3TA, UK

^b School of Chemistry and Pharmaceutical Engineering, Qilu University of Technology, Jinan 250353, PR China

^c School of Chemistry, Cardiff University, CF10 3AT, UK

^d State Key Laboratory of Advanced Technology for Materials Synthesis and Processing, Wuhan University of Technology, Wuhan 430070, PR China

article info

abstract

Two fluorinated diazomethanes were synthesized, and used for the modification of polystyrene XAD4, polyacrylate MAC-3, filter paper, and Hybond™ membrane. The structure of modified polymers was confirmed by XPS and solid-state NMR spectra, with a surface loading of 8.28×10^{12} – 1.68×10^{13} molecules per cm^2 . Water contact angle values, which increased from 0L to 128.51L (for filter paper) and 120.02L (for Hybond™ membrane), demonstrated hydrophobicity.

Keywords:

Diaryldiazomethane

Fluoroalkyl

Surface modification

Hydrophobic

Post-polymerisation

1. Introduction

The hydrophobic behavior of solid surfaces has a wide diversity of applications such as self-cleaning surfaces, high adhesive surfaces, antifogging coatings, and antireflection coatings [1]. Different preparation strategies have been developed to fabricate hydrophobic surfaces [2,3], which include nanoparticles doping [4–6], the introduction of fluorine or silicic or long alkyl chain chemistry [7–10], and plasma treatment [11,12]. He et al. [13,14] used CF_4 plasma modification for the conversion of a hydrophilic membrane into a hydrophobic membrane but a simple, universal and efficient chemical method for the direct hydrophobic modification of a wide range of polymers would be highly desirable. Modifications have been developed [15] using carbenes [16] or nitrenes [17], and we have developed a strategy of modification through carbene insertion reactions derived from aryldiazomethanes [18–25], which benefits from a short synthetic route and mild reaction conditions.

2. Experimental

Full experimental details and results are included in the [Electronic Supporting Information](#).

† Corresponding author.


E-mail address: mark.moloney@chem.ox.ac.uk (M.G. Moloney).

Polymer Beads (6a–b, 7a–b). To a solution of fluorodiazomethane 5a–b in dichloromethane (10 mL) was added the required polymer, and then the mixture was concentrated under vacuum. The polymer was collected and heated at 120 °C in an open flask for 30 min. The resulting solid was washed with acetone for 3 times and dried to yield the functionalized polystyrene 6a–b and polyacrylate 7a–b.

Polymer Sheets (8a–b, 9a–b). To a solution of fluorodiazomethane 5a–b in dichloromethane (2 mL) was added the required sheet. After it absorbed the solution completely, polymer sheet was taken out and dried under N_2 flow. Then, it was heated in an open beaker to 120 °C for 30 min. The resulting sheet was washed with acetone for 3 times and dried to yield the functionalized filter paper 8a–b and Hybond 9a–b.

3. Results and discussion

In this paper, we report the use of this approach to introduce perfluoroalkyl groups into diazomethanes, to achieve the modification of different polymer beads and sheets, giving surfaces with hydrophobic properties. 4-Aminobenzophenone was used to react with a perfluoroalkyl iodide to obtain fluorobenzophenones 2a–b, followed by acetylation to generate fluorobenzophenones 3a–b (Scheme 1). These were treated with hydrazine monohydrate to generate fluorohydrazones 4a–b, which were in turn oxidized with

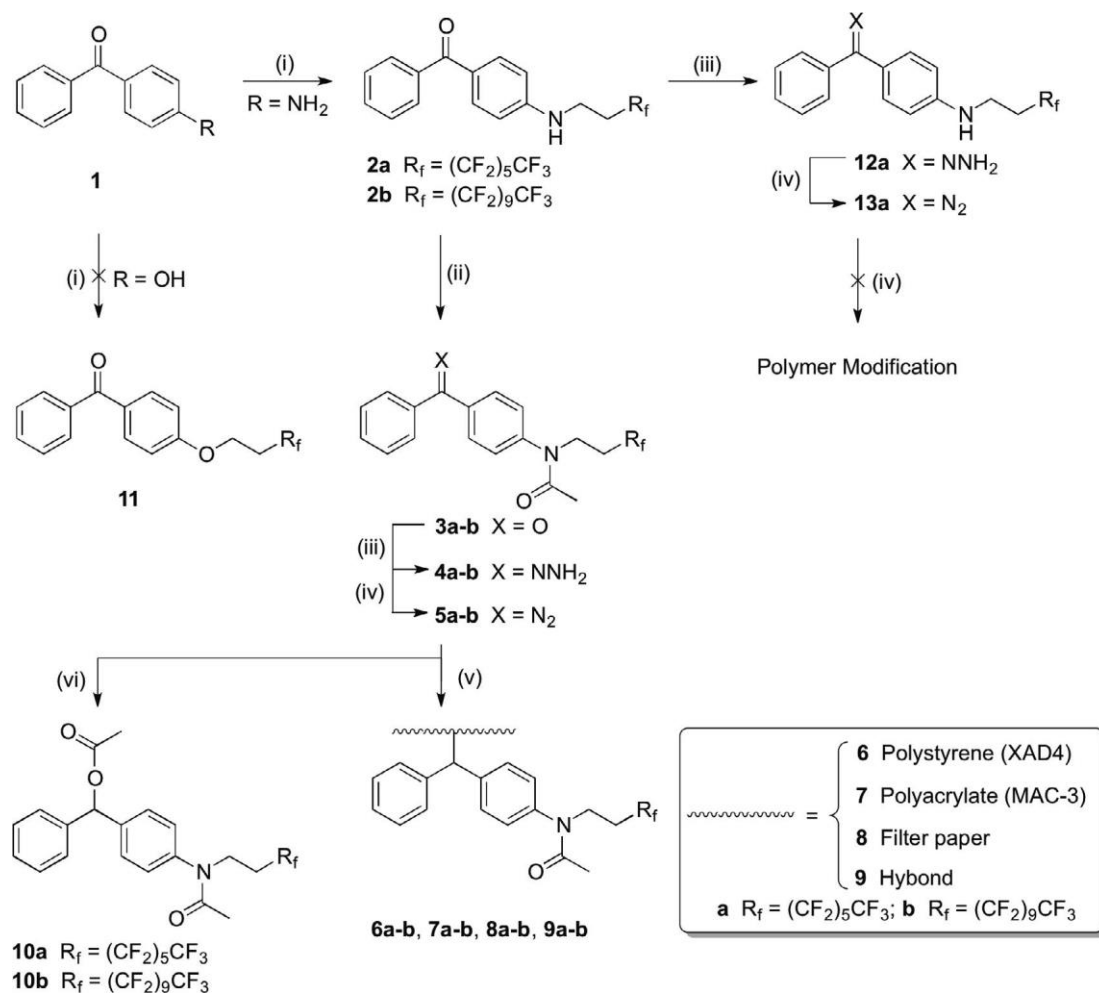

Scheme 1. Synthesis of precursor, and modification of polymers. Conditions: (i) $\text{I}(\text{CH}_2)_2\text{C}_n\text{F}_{2n+1}$, 140 LC, 18 h, (26–52%); (ii) K_2CO_3 , DMAP, DCM, r.t., 3 h, (88–96%); (iii) $\text{NH}_2\text{NH}_2 \cdot \text{H}_2\text{O}$, HOAc, EtOH, reflux, 40 h, (83–90%); (iv) MnO_2 , Na_2SO_4 , KOH, DCM, r.t., 2 h (98–99%); (v) 120 LC; (vi) HOAc, Et₂O, r.t., 30 min (50–55%).

manganese dioxide to obtain fluorodiazomethanes 5a–b. Before these materials were applied to the preparation of modified polymers polystyrene XAD4, polyacrylate MAC-3, filter paper, and Hybond™ 6–9 respectively (vide infra), their chemical reactivity was assessed by reaction with acetic acid to give the esters 10a–b, and compared to that of several other diazomethanes.

For fluorodiazomethane 5a in dichloromethane, clear changes of the UV spectra at 519 nm were observed after acetic acid was added, and these could be used for kinetic studies; details of the analysis are included in the Supplementary Information (Fig. 1, SI and Table 1, SI), but significantly, compounds 5a–b give a good balance of stability and reactivity, which is required in a surface modifying agent.

Of interest is that this strategy was not suitable for the formation of fluorobenzophenone 11 from 4-hydroxybenzophenone regardless of the base used to deprotonate the phenolic hydroxyl. Furthermore, although fluorobenzophenone 2a could be converted to fluorodiazomethane 13a in the usual way, it proved to be too reactive to be used for subsequent modification, and this outcome emphasized the importance of the presence of the acetyl group for the successful isolation of diazo 5a–b.

Polystyrene XAD4, MAC-3, filter paper, and Hybond™ membrane were used as substrates for surface modification with diazo 5a–b; their colour changed from white to light yellow after modification, consistent with the introduction of aromatic functionality. Clear changes of surface elements were found by XPS analysis and

by solid state NMR spectroscopy (full details are given in the Supplementary Information (Figs. 2 and 3, SI and Table 2, SI)), for which the carbon spectra of 6a by ^{19}F / ^{13}C CP showed the presence of the perfluoroalkyl groups. This confirmed the successful modification with fluorodiazomethanes 5a–b. The surface loadings of 6a–b could be determined by a combination of surface area measurement by BET analysis and quantitation of nitrogen content by elemental combustion analysis (full details are given in the Supplementary Information (Table 3, SI)), and are very similar to the values that have been reported [26].

The surface-loaded fluoroalkyl chains generated hydrophobic behavior, which could be clearly demonstrated from the water contact angle of the modified filter paper and Hybond™. However, the contact angle increased to as large as 128.51° for treated filter paper 8b and 120.02° for treated Hybond™ 9b after fluorine was introduced onto their surface (Table 1, water of unmodified filter

Table 1
Water contact angle of filter paper and Hybond™ membrane before and after modification.

Polymer sheets	Unmodified	a (C ₆ F ₁₃ -Modified)	b (C ₁₀ F ₂₁ -Modified)
8 (Filter paper)	0L	120.0 ± 4.4L	128.5 ± 0.4L
9 (Hybond membrane)	0L	112.6 ± 7.6L	120.0 ± 2.2L

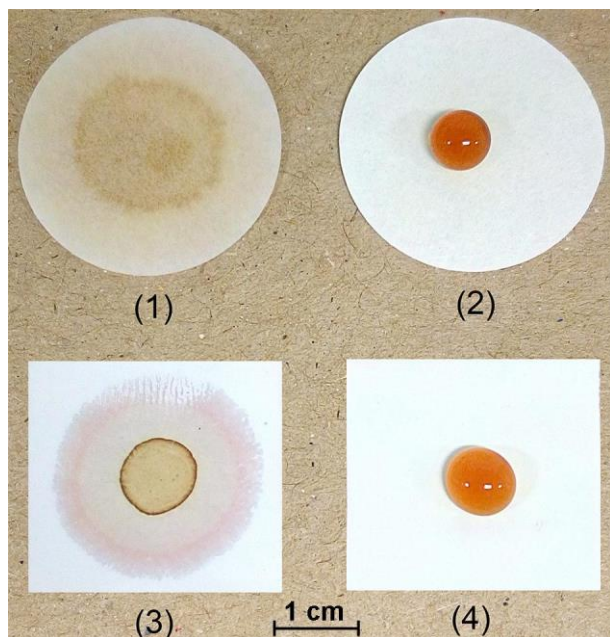


Fig. 1. Hydrophobic behavior: (1) unmodified filter paper; (2) 8b; (3) unmodified Hybond™; (4) 9b.

paper or Hybond™ is 0L). Fig. 1 shows the hydrophobic behavior of modified polymer sheets.

4. Conclusion

The effect of fluorination on surface wettability is well known [27–29], and often achieved with plasma mediated fluorination and while although other approaches have been developed [30–33], the work reported here offers a direct and effective chemical reagent which makes use of comparatively rare fluoro-substituted carbenes [34] suitable for the introduction of fluorine to diverse surfaces under mild reaction conditions to give a hydrophobic polymer surface on polystyrene, polyacrylate, filter paper, and Hybond™ substrates.

Acknowledgement

This work is financially supported by the National Natural Science Foundation of China (No. 21406121).

References

- [1] K. Liu, X. Yao, L. Jiang, Recent developments in bio-inspired special wettability, *Chem. Soc. Rev.* 39 (8) (2010) 3240–3255.
- [2] P. Roach, N.J. Shirtcliffe, M.I. Newton, Progress in superhydrophobic surface development, *Soft Matter* 4 (2) (2008) 224–240.
- [3] X. Zhang, F. Shi, J. Niu, Y. Jiang, Z. Wang, Superhydrophobic surfaces: from structural control to functional application, *J. Mater. Chem.* 18 (6) (2008) 621–633.
- [4] Y. Tian, L. Jiang, Wetting: intrinsically robust hydrophobicity, *Nat. Mater.* 12 (4) (2013) 291–292.
- [5] R. Wu, S. Liang, A. Pan, Z. Yuan, Y. Tang, X. Tan, D. Guan, Y. Yu, Fabrication of nanostructured super-hydrophobic film on aluminum by controllable immersing method, *Appl. Surf. Sci.* 258 (16) (2012) 5933–5937.

- [6] G. Zhu, Y. Su, P. Bai, J. Chen, Q. Jing, W. Yang, Z.L. Wang, Harvesting water wave energy by asymmetric screening of electrostatic charges on a nanostructured hydrophobic thin-film surface, *ACS Nano* 8 (6) (2014) 6031–6037.
- [7] Z. Guo, F. Zhou, J. Hao, W. Liu, Stable biomimetic super-hydrophobic engineering materials, *J. Am. Chem. Soc.* 127 (45) (2005) 15670–15671.
- [8] S.-C. Luo, S.S. Liour, H.-H. Yu, Perfluoro-functionalized PEDOT films with controlled morphology as superhydrophobic coatings and biointerfaces with enhanced cell adhesion, *Chem. Commun.* 46 (26) (2010) 4731–4733.
- [9] R.G. Wankhede, S. Morey, A.S. Khanna, N. Biribilis, Development of water-repellent organic–inorganic hybrid sol–gel coatings on aluminum using short chain perfluoro polymer emulsion, *Appl. Surf. Sci.* 283 (2013) 1051–1059.
- [10] T. Darmanin, F. Guittard, pH- and voltage-switchable superhydrophobic surfaces by electro-copolymerization of EDOT derivatives containing carboxylic acids and long alkyl chains, *ChemPhysChem* 14 (11) (2013) 2529–2533.
- [11] A. Cifuentes, S. Borrás, Comparison of Two different plasma surface-modification techniques for the covalent immobilization of protein monolayers, *Langmuir* 29 (22) (2013) 6645–6651.
- [12] I. Sadeghi, A. Aroujalian, A. Raisi, B. Dabir, M. Fathizadeh, Surface modification of polyethersulfone ultrafiltration membranes by corona air plasma for separation of oil/water emulsions, *J. Membr. Sci.* 430 (2013) 24–36.
- [13] X. Wei, B. Zhao, X.-M. Li, Z. Wang, B.-Q. He, T. He, B. Jiang, CF₄ plasma surface modification of asymmetric hydrophilic polyethersulfone membranes for direct contact membrane distillation, *J. Membr. Sci.* 407–408 (2012) 164–175.
- [14] C. Yang, X.-M. Li, J. Gilron, D.-F. Kong, Y. Yin, Y. Oren, C. Linder, T. He, CF₄ plasma-modified superhydrophobic PVDF membranes for direct contact membrane distillation, *J. Membr. Sci.* 456 (2014) 155–161.
- [15] A. Blencowe, W. Hayes, Development and application of diazirines in biological and synthetic macromolecular systems, *Soft Matter* 1 (3) (2005) 178.
- [16] S. Ghiassian, H. Ismaili, B.D. Lubbock, J.W. Dube, P.J. Ragogna, M.S. Workentin, Photoinduced carbene generation from diazirine modified task specific phosphonium salts to prepare robust hydrophobic coatings, *Langmuir* 28 (33) (2012) 12326–12333.
- [17] F. Shi, J. Niu, Z. Liu, Z. Wang, M. Smet, W. Dehaen, Y. Qiu, X. Zhang, To adjust wetting properties of organic surface by in situ photoreaction of aromatic azide, *Langmuir* 23 (3) (2007) 1253–1257.
- [18] K.M. Awenat, P.J. Davis, M.G. Moloney, W. Ebenezer, A chemical method for the convenient surface functionalisation of polymers, *Chem. Commun.* 41 (8) (2005) 990–992.
- [19] M.G. Moloney, Functionalized polymers by chemical surface modification, *J. Phys. D: Appl. Phys.* 41 (17) (2008) 174006.
- [20] C. Choong, J.P. Griffiths, M.G. Moloney, J. Triffitt, D. Swallow, Direct introduction of phosphonate by the surface modification of polymers enhances biocompatibility, *React. Funct. Polym.* 69 (2) (2009) 77–85.
- [21] J.P. Griffiths, B. Maliha, M.G. Moloney, A.L. Thompson, I. Hussain, Surface functional polymers by post-polymerization modification using diarylcarbenes, *Langmuir* 26 (17) (2008) 14142–14153.
- [22] A. Aphaiwong, M.G. Moloney, M. Christlieb, Surface functional polymer library by post-polymerisation modification using diarylmethylenes, *J. Mater. Chem.* 22 (47) (2008) 24627–24636.
- [23] C. Choong, J.S. Foord, J.P. Griffiths, E.M. Parker, L. Baiwen, M. Bora, M.G. Moloney, Post-polymerisation modification of surface chemical functionality and its effect on protein binding, *New J. Chem.* 36 (5) (2012) 1187–1200.
- [24] C.L. Bagwell, D.M.L. Leonard, J.-P. Griffiths, M.G. Moloney, N.J. Stratton, D.P. Travers, Post-polymerization modification of materials using diaryldiazomethanes: changes to surface macroscopic properties, *Macromol. React. Eng.* 8 (2) (2014) 170–180.
- [25] G.W. Nelson, E.M. Parker, K. Singh, C.F. Blanford, M.G. Moloney, J.S. Foord, Surface characterization and in situ protein adsorption studies on carbene-modified polymers, *Langmuir* 31 (2015) 11086–11096.
- [26] P. Yang, M.G. Moloney, Surface modification of polymers with bis(arylcabene)s from bis(aryldiazomethane)s, *RSC Adv.* 6 (2008) 111276–111290.
- [27] K. Tokuda, T. Ogino, M. Kotera, T. Nishino, Simple method for lowering poly (methyl methacrylate) surface energy with fluorination, *Polym. J.* 47 (2015) 66–70.
- [28] F.J. du Toit, R.D. Sanderson, W.J. Engelbrecht, J.B. Wagener, The effect of surface fluorination on the wettability of high density polyethylene, *J. Fluorine Chem.* 74 (1995) 43–48.
- [29] L.J. Hayes, Surface energy of fluorinated surfaces, *J. Fluorine Chem.* 8 (1976) 69–88.
- [30] Y. Yu, X. Wang, Chemical modification of polymer surfaces for advanced triboelectric nanogenerator development, *Extreme Mech. Lett.* 9 (2016) 514–530.
- [31] J. Hubert, J. Mertens, T. Dufour, N. Vandecasteele, F. Reniers, P. Viville, R. Lazzaroni, M. Raes, H. Terryn, Synthesis and texturization processes of (super)-hydrophobic fluorinated surfaces by atmospheric plasma, *J. Mater. Res.* 30 (2015) 3177–3191.
- [32] T. Darmanin, F. Guittard, Superoleophobic surfaces with short fluorinated chains?, *Soft Matter* 9 (2013) 5982–5990.
- [33] A.P. Kharitonov, L.N. Kharitonova, Surface modification of polymers by direct fluorination, *Pure Appl. Chem.* 81 (2009) 451–471.
- [34] C. Buron, E.M. Tippmann, M.S. Platz, Generation and characterization of new fluoro-substituted carbenes, *J. Phys. Chem. A* 108 (6) (2004) 1033–1041.