

This is an Open Access document downloaded from ORCA, Cardiff University's institutional repository: <https://orca.cardiff.ac.uk/id/eprint/165005/>

This is the author's version of a work that was submitted to / accepted for publication.

Citation for final published version:

Zhang, Jing, Mylonas, Petros and Banerjee, Avijit 2023. Mineralizing agents to manage early carious lesions. Part I: mode of action. Dental Update 50 (6) 10.12968/denu.2023.50.6.490

Publishers page: <https://doi.org/10.12968/denu.2023.50.6.490>

Please note:

Changes made as a result of publishing processes such as copy-editing, formatting and page numbers may not be reflected in this version. For the definitive version of this publication, please refer to the published source. You are advised to consult the publisher's version if you wish to cite this paper.

This version is being made available in accordance with publisher policies. See <http://orca.cf.ac.uk/policies.html> for usage policies. Copyright and moral rights for publications made available in ORCA are retained by the copyright holders.



Mineralising agents to manage early carious

lesions – part I: mode of action

Abstract

Dental caries remains a major global health challenge affecting millions of people worldwide, with both major health and financial implications. The minimum intervention oral healthcare (MIOC) delivery framework aims to improve caries management through early diagnosis and the use of remineralisation strategies in primary and secondary preventive approaches. The landmark discovery of fluoride in caries remineralisation resulted in an increase in research on such non-operative approaches. With an improved understanding of the biochemistry of caries and the demineralisation-remineralisation balance within dental hard tissues, researchers and clinicians currently seek new therapies to improve the non-operative management of early carious lesions. New remineralisation technologies have been introduced in recent years, with varying chemistries, modes of action and degrees of success.

This paper, the first of a two part series, will explore the chemistry and mode of action of currently available remineralisation technologies, outlining their clinical effectiveness and use in dental caries management.

Clinical relevance

A scientific understanding of ever-evolving remineralisation technologies is necessary to ensure clinicians are aware of the available options, their advantages and disadvantages, as well as to ensure these technologies are utilised correctly in different clinical scenarios.

Objectives

The reader should understand the chemistry and mechanism of action of currently available early carious lesion remineralisation therapies.

INTRODUCTION

Dental caries is one of the world's most prevalent non-communicable diseases, affecting adversely approximately 3.5 billion people, resulting in both a great health and financial burden^{1,2}. Carious lesions start from dissolution of hydroxyapatite crystals at the tooth surface, at an atomic level, which occurs following the formation and stagnation of the dental plaque biofilm, if left undisturbed³. If no intervention occurs, the caries process will remain active and the lesion will progress which increases the complexity of its management³. The minimum intervention oral care (MIOC) philosophy applied to caries management has moved from invasive conventional operative management to more micro- / minimally invasive early interventions, with an increasing emphasis placed on early diagnosis and non-operative preventive strategies, among which, remineralisation plays a major part⁴⁻⁷. The early disruption of the caries process negates the requirement for extensive operative intervention later, leading to the preservation of more tooth structure and reducing the burden and complexity of future dental treatment⁴.

Human saliva is naturally saturated with calcium and phosphate ions necessary for remineralisation. This is an important part of the natural homeostatic mechanism maintaining the demineralisation-remineralisation balance that occurs on exposed dental hard tissue surfaces. The clinical efficacy of saliva on its own to maintain this demineralisation-remineralisation balance can be affected by many factors including saliva quality and quantity (xerostomia), the latter commonly being affected by patient polypharmacy; these factors affect adversely patients' susceptibility to caries. As a result, adjunctive remineralisation products, protocols and strategies are required to supplement this process^{8,9}.

The purpose of this two-part review is to provide a comprehensive review of the mineralisation technologies available and to discuss comparatively the clinical efficacy of these strategies in dental caries management.

CHEMISTRY OF REMINERALISATION - MODE OF ACTION

The natural formation of enamel (amelogenesis) is a complex biomineralisation process involving cellular activity¹⁰. Proteins self-organise to regulate the crystallisation of hydroxyapatite in an ordered manner, i.e., the extracellular protein matrix continuously forms when enamel crystals grow in length and the enamel thickens, followed by the transition and maturation stage when the protein matrix degrades as crystals grow in width and is eventually removed upon the completion of enamel formation. Therefore, mature enamel is acellular and once demineralised, any repair cannot occur through autonomous biomineralisation, but through extrinsic remineralisation processes. Remineralisation (perhaps better termed mineral deposition) can be described as the relatively disordered deposition of apatitic minerals onto / within the demineralised tissue. Efforts in investigating these remineralisation processes have resulted in several commercialised agents available for clinical use. Depending on the mechanism, these can be categorised into the following groups^{8,11}:

1. Fluoride-based systems
2. Non-fluoride-based systems
3. Biomimetic systems.

Fluoride-based systems

Fluoride is often considered the “gold standard” in enamel remineralisation. The mechanisms by which fluoride facilitates enamel mineralisation have been well documented. In an aqueous environment saturated with mineral ions and with a pH > 5.5, fluoride will absorb into the

demineralised enamel acting as nucleation sites and attracting calcium ions due to its electronegative ionic charge¹². It is suggested that a set of reactions including ion-exchange, chemisorption and hydrolysis can occur when fluoride reacts with hydroxyapatite (HA), which eventually results in transformation of HA to fluorapatite (FA) or fluoridated hydroxyapatite (FHA)¹³. FA and FHA have lower solubility in oral fluids at the critical pH for carious lesion formation (pH 5.5) thus increasing its resistance to demineralisation¹⁴.

Fluoride delivers significant remineralisation potential at a low concentration (sub-ppm level)^{13,15,16}, but with a significant positive dose-response, with increased mineral gain with an increasing fluoride concentration¹⁷. However, a recent in-vitro study noted that the fluoride dose-response may also be dependent on the severity of the lesion, i.e. the earlier the lesion, the better the dose-response, with possible reasons being that in more demineralised lesions the developed surface zone blocks the influx of mineral ions due to hypermineralisation and/or the lack of soluble mineral ions leaves more acid-resistant minerals in the lesion¹⁸.

The clinical mode of action of fluoride in remineralisation / mineral deposition is more sophisticated as biological factors may affect its efficacy. Fluoride can diffuse into the natural plaque biofilm which may act as a reservoir to maintain fluoride concentration in the oral fluids close to the tooth surface¹⁹. When the biofilm is immature, in-vitro studies have revealed that fluoride failed to promote remineralisation significantly, implying that elevated levels of fluoride in plaque and saliva exert a significant impact^{20,21}. The levels of fluoride in plaque is associated with many factors including plaque disruption rate and pH²². In addition, calcium fluoride (CaF₂) may form alongside FA and FHA and be deposited onto the enamel surface. CaF₂ is readily soluble in acidic pH when it dissolves and releases both calcium and fluoride into oral fluids, therefore acting as an alternative reservoir of calcium²³. However, high-dose fluoride leads to excessive formation of CaF₂, which may in turn clog the lesion surface, resulting in reduced remineralisation capacity²⁴.

Non-fluoride-based systems

Non-fluoridated mineralisation agents can be further subcategorised into pH modifiers, and calcium-phosphate systems²⁵ (see Table 1).

pH modifiers

Generally, pH modifiers promote remineralisation by affecting the pH of the microenvironment. An example of this is xylitol, a non-fermentable, non-acid-producing sugar substitute. Xylitol can help maintain the pH of dental biofilm above 5.5 and meanwhile increase the flow rate of the stimulated saliva which has a higher concentration of calcium and phosphate, thereby creating a suitable environment for remineralisation²⁶. Likewise, arginine is an amino-acid which has also been found to boost remineralisation through raising pH in the oral environment due to the production of ammonia after the amino acid is deaminated by arginine deaminase, found within saliva²⁷. However, high-quality clinical evidence of pH-modifying remineralisation agents is scarce and sometimes contradicting. Therefore these agents show potential but more clinical trials are required before more robust conclusions can be drawn^{28,29}.

Calcium-phosphate systems

Several compounds can be classified as calcium-phosphate remineralisation agents, including casein phosphopeptide-amorphous calcium phosphate (CPP-ACP), bioactive glasses, calcium silicate, functional tricalcium phosphate (f-TCP), nano-hydroxyapatite (n-HA) and amorphous calcium phosphate (ACP).

Though the specific mode of action of these agents differs, their chemistry is broadly similar. They all release calcium phosphate ions into the oral fluid and maintain concentrations that are supersaturated with respect to hydroxyapatite (HA), therefore resulting in mineral gain at the surface of carious lesions. For example, the amino acid sequence “-Ser(P)-Ser(P)-Ser(P)-Glu-Glu-“ from CPP is found to stabilise calcium and phosphate by formation of amorphous phosphate nano-clusters, approximately 2nm in size³⁰. These nano-complexes prevent crystal growth to the critical size needed

for nucleation and phase transformation and hence act as a mineral ion supplier for later remineralisation.

When introduced into an aqueous environment, calcium sodium phosphosilicate bioglasses (bioactive glasses) can release calcium and phosphate as well as increase the pH through surface ion exchange reactions^{31,32}. These result in deposition of hydroxycarbonate apatite (HCA)-coated glass particles onto carious enamel surfaces³³. The glass particles can bind to enamel surfaces and continually release mineral ions to facilitate mineralisation³⁴.

Likewise, calcium silicates have a similar mode of action to bioglasses in remineralisation, by releasing calcium via ion exchange from surface reactions with body fluids³⁵. Recent in-vitro studies have indicated that calcium silicate can precipitate HA and help repair demineralised enamel³⁶.

ACP, n-HA and f-TCP are similar histologically to enamel apatite⁸. ACP is an unstable, transitional apatitic phase which, after formation, can release calcium and phosphate ions for remineralisation before transformation to a thermodynamically stable phase such as HA³⁷. n-HA are nanosized hydroxyapatite particles that exhibit significantly increased surface area. The precise mechanism that n-HA enhances remineralisation is unclear; some studies suggest that the large surface area allows n-HA particles to directly bind to enamel surface defects like a filler and attract calcium and phosphate ions to grow^{38,39}. Others claim n-HA's function as a calcium phosphate reservoir⁴⁰. With respect to f-TCP, originally designed to boost fluoride remineralisation efficacy, its functionalisation by organic compounds allows a protective barrier to prevent calcium from reacting prematurely with fluoride, hence providing bioavailable calcium when interacting with saliva⁴¹.

Biomimetic systems

Biomimetic approaches have gained increasing interest in recent years. Self-assembling peptides are an analogue to enamel matrix proteins which could guide oriented apatite growth. P11-4 peptides, for example, are tailored for subsurface remineralisation. Some studies indicate that P11-4 can diffuse into the carious lesion body, self-assemble into 3D hierarchical structures under highly ionic

concentration to provide nucleation sites for mineral ions, therefore favouring remineralisation^{42,43}. Although laboratory studies have found conflicting results regarding its efficacy in remineralising incipient carious lesions^{44,45}, recent clinical trials showed that P11-4 induced significantly greater remineralisation than other agents including f-TCP and fluoride^{46,47}. This material has been successfully launched as Curodont™ by Credentis for dental professionals.

HISTOLOGICAL CHARACTERISTICS FOR MINERALISATION

Incipient carious lesions (white spot lesions (WSLs)) present clinically as a white, chalky and roughened enamel surface due to the light scattering that occurs due to the difference in refractive index between the air/water in the porosities within the lesion and mineral, which intensifies with air-drying. This poses an aesthetic and functional problem⁴⁸. A histological diagram is shown in Figure 1. A recent in-vitro pH-cycling study monitored the colour change in artificial WSLs using a spectroradiometer and attributed the greatest reversal of the white appearance observed in 5000 ppm fluoride group to remineralisation, which was evidenced by scanning electron microscopy (SEM) and electron microprobe analysis⁴⁹. However, despite this remineralisation, the white spot remained clinically evident after fluoride application. Similarly, CPP-ACP was found to show a significantly greater colour reversal compared to artificial saliva in-vitro⁵⁰. Further examinations suggested that such colour change was associated with mineral deposition filling the microporosities at the lesion surface. However, another in-situ study compared the aesthetic characteristics of artificial WSLs remineralised by 5000 ppm fluoride, bioglass and CPP-ACP and found no significant difference amongst all materials tested⁵¹.

Carious lesions are unique because histologically they consist of a well mineralised surface zone in which the porosity is 1-2%, overlying the body of the lesion which accounts for 25-50% porosity⁵² (see Figure 1). Remineralisation will affect these histological zones and consequently induce a series of changes.

The remineralisation capabilities in the surface zone have been evidenced by studies employing various remineralisation agents. For example, in an in-vitro study, Milly et al. demonstrated that bioglass, either pure or modified with polyacrylic acids, could precipitate apatitic crystals and assist the growth of the existing enamel prisms, therefore filling the superficial interprismatic spaces⁵³. Some reports predict that the recrystallisation mode depends on the calcium level of the solution; a low calcium concentration favours crystallisation on existing damaged crystals whilst higher

concentrations may support nucleation and new crystal formation⁵⁴. Other agents possess similar surface remineralisation efficacy, including fluoride, CPP-ACP, f-TCP and n-HA^{53,55-57}. The mineral gain in the surface zone can be measured as the recovery of surface microhardness resulting from the micro-structure reinforcement by the newly formed crystals. A recent in-vitro pH-cycling study by Wang et al. comparing bioglass, CPP-ACP and fluoride on surface remineralisation suggested that treatment with these agents yielded significantly greater surface hardness recovery than in controls, which correlated well with morphological observations by SEM⁵⁸. Caution is required as techniques such as SEM and microhardness are surface characterisations only. The Knoop microhardness indenter, for example, produces indentations with limited penetration to approx. 1.5 μm ⁵⁹. Thus the interpretation of these results must be made with care when extrapolating to the clinical situation.

The sub-surface body of the incipient carious lesion accounts for its bulk and mineral infill in this part is crucial to successful long term lesion repair. Some pH-cycling studies showed that by increasing the concentration, fluoride could diffuse through the depth of the lesion and initiate a deeper remineralisation⁶⁰. Fluoride tablets (4350 ppm) exhibited extensive remineralisation from the base of lesions, resulting in significant reduction in lesion depth, when compared to 1450 ppm fluoride. Polarised light microscopy also showed an increased translucent zone after high-dose fluoride application, representing mineral infill in the inner part of the lesion. However, a recent in-situ study suggested the opposite. Microradiographic observations by Amaechi et al. indicated that HA induced a more homogeneous remineralisation throughout the lesion depth than 500 ppm fluoride, where remineralisation occurred mostly in the surface zone⁶¹. Nevertheless, both studies exhibited clear lamination after treatment, implying that the diffusion pathways in the lesion surface were blocked by the superficial mineral deposition. This is in agreement with previous studies⁶².

Similarly, CPP-ACP claims to possess subsurface remineralisation capabilities⁶³. Longitudinal microhardness and microradiography suggested that CPP-ACP could favour more subsurface mineral regain than other agents including calcium silicate and fluoride^{57,64}. However, it was noted that the

lesion surface remineralised by CPP-ACP exhibited comparably weaker mechanical properties. The conjecture was that newly precipitated mineral by CPP-ACP was less acid-resistant, hence the pathways for ion diffusion remained open. A comparative study, on the other hand, suggested that CPP-ACP and fluoride were not superior to HA in remineralising the subsurface lesion; all mineral gain followed an outside-inwards direction and predominately took place in/on the lesion surface⁶⁵. These contradictory findings may arise from the disparities in study design, including concentration of the agent, study duration, type of study, etc.

CHALLENGES FOR REMINERALISATION

Deep mineral gain within the body of the carious lesion remains the challenge for remineralisation strategies. The porosity of the lesion surface zone is relatively small and can be more easily occluded when topical agents react and readily deposit on the surface, thus hindering ion penetration into the lesion depth. The lesion surface is arrested at the sacrifice of the lesion body in which the caries process and sub-surface damage may still continue. The salivary pellicle, a tenacious semi-permeable organic layer on the enamel surface, retards transportation of ionic matter across the enamel⁶⁶. In-vitro studies have demonstrated that this pellicle could inhibit remineralisation on artificially formed WSLs⁶⁷. It is therefore the delivery of calcium and phosphate ions into the depths of a lesion that controls remineralisation. Figure 2 demonstrates the influence of mineral ions (concentration and exposure time) on the remineralisation of incipient enamel lesions.

Some agents, such as self-assembling peptides and CPP-ACP, claim to possess the potential for subsurface remineralisation. The mechanisms were discussed earlier. Although CPP-ACP has been shown to boost subsurface remineralisation, a recent study found that extended application time with CPP-ACP failed to produce additive remineralisation effect⁶⁴. Pre-conditioning the lesion surface to create better conditions for diffusion may provide an alternative route. Self-assembling peptides require conditioning through use of oral prophylaxis to remove biofilms and existing mineral deposits

which may prevent peptide monomers from penetrating⁶⁸. Meanwhile, acid etching the lesion surface could also be considered to improve diffusion. Similar efforts have also been reported for other agents. For example, subsurface remineralisation using a bioglass slurry was enhanced by surface pre-conditioning with air-abrasion using bioglass particles modified by polyacrylic acids⁶⁹. Mineral depositions were observed at approximately 40 µm depth. Likewise, subsurface remineralisation, to some degree, was enhanced by surface pre-conditioning with chitosan before bioglass application⁷⁰. However, a dense layer consisting of newly deposited minerals was found to cover the lesion surface after the remineralisation regime. However, will this level of subsurface remineralisation be effective long-term? Perhaps these surface pre-conditioning techniques may require continuous / multiple applications by oral healthcare professionals, making home-based treatment difficult. Thus, designing an effective method for mineral ion penetration is paramount for new effective remineralisation strategies.

The speed of ion release is another challenge especially for toothpastes and mouthwash carriers. Toothpastes cannot release active ingredients until dispensed and having interacted with water or saliva. Other factors such as toothbrush head geometry and filament size, saliva quality and secretion rate are further complexities to consider⁷¹. Mouthrinse has better ion-release potential. However, retention of such mineralising agents remains an issue. The active phase of these agents is transient after brushing or rinsing, because of the diluting effect caused by abrasive challenges by tongue, cheek movement, and/or pH change^{72,73}.

THE FUTURE OF BIOMIMETIC REMINERALISATION

In recent years, attention has been drawn to the biomineralisation strategy for carious lesion repair, which aims to incorporate enamel proteins such as amelogenin to induce remineralisation. Tooth enamel is the hardest tissue **in** the human body and this unique characteristic is reportedly due to its delicate 7-level hierarchical structure⁷⁴. Current commercialised remineralisation agents can achieve

mineral gain in the lesion, but to the best of the authors' knowledge seldom replicate the hierarchical structure of enamel during remineralisation. Amelogenins constitute 90% of matrix proteins involved in the process of enamel growth and the self-assembly ability is thought to be pivotal in forming the complicated hierarchical structure of enamel⁷⁵. Molecular mechanisms include selective binding to specific crystal facets to regulate orientated crystal growth and reaction with ACP to form intermediate pre-nucleation clusters that transform into organised crystals in subsequent stages⁷⁵. Remineralisation efficacy of amelogenin and its derivatives have been investigated. A hydrogel composed of chitosan-amelogenin rP172 was found to biomimetically form mineral depositions with enamel-like crystals on both the surface and the subsurface of acid-etched and artificial carious lesions after pH-cycling for seven days^{76,77}. Leucine-rich amelogenin peptide, an amelogenin derivative, has also been found to reduce lesion depth and facilitate biomimetic reconstruction of enamel⁷⁸. Meanwhile, there are certain concerns regarding amelogenin strategy, including the extraction and storage of amelogenins and duration required for the treatment¹¹. However, clinical evidence is sparse, hence requiring more research to prove clinical efficacy.

CONCLUSIONS

Remineralisation of early carious enamel lesions has seen promising progress in recent decades. Fluoride, calcium phosphate and biomimetic approaches and their combinations could successfully repair the surface and, to some degree, the subsurface zones of such incipient carious lesions. The lack of sufficient remineralisation in the lesion body remains the greatest challenge for all commercialised mineralising agents. New biomineralisation strategies employing amelogenin and its derivatives may provide an alternative route which has the potential to restore the hierarchical structure of tooth enamel. Extensive clinical investigations are demanded to prove the clinical benefits for these remineralisation agents.

REFERENCES

- 1 James SL, Abate D, Abate KH, Abay SM, Abbafati C, Abbasi N *et al.* Global, regional, and national incidence, prevalence, and years lived with disability for 354 diseases and injuries for 195 countries and territories, 1990–2017: a systematic analysis for the Global Burden of Disease Study 2017. *Lancet* 2018; **392**: 1789–1858.
- 2 Bernabé E, Marcenes W. Can minimal intervention dentistry help in tackling the global burden of untreated dental caries? *Br Dent J* 2020; **229**: 487–491.
- 3 Kidd EAM, Fejerskov O. What constitutes dental caries? Histopathology of carious enamel and dentin related to the action of cariogenic biofilms. *J Dent Res* 2004; **83**: 2002–2005.
- 4 Banerjee A. Minimal intervention dentistry: Part 7. Minimally invasive operative caries management: Rationale and techniques. *Br Dent J* 2013; **214**: 107–111.
- 5 Banerjee A. ‘Minimum intervention’ – MI inspiring future oral healthcare? *Br Dent J* 2017; **223**: 133–135.
- 6 Banerjee A. Minimum Intervention (MI) Oral Healthcare Delivery Implementation – Overcoming the Hurdles. *Prim Dent J* 2017; **6**: 28–33.
- 7 Banerjee A. Minimum intervention oral healthcare delivery - is there consensus? *Br Dent J* 2020; **229**: 393–395.
- 8 Cochrane NJ, Cai F, Huq NL, Burrow MF, Reynolds EC. New approaches to enhanced remineralization of tooth enamel. *J Dent Res* 2010; **89**: 1187–1197.
- 9 He T, Li X, Dong Y, Zhang N, Zhong Y, Yin W *et al.* Comparative assessment of fluoride varnish and fluoride film for remineralization of postorthodontic white spot lesions in adolescents and adults over a 6-month period: A single-center, randomized controlled clinical trial. *Am J Orthod Dentofac Orthop* 2016; **149**: 810–819.

- 10 Ruan Q, Moradian-Oldak J. Amelogenin and enamel biomimetics. *J Mater Chem B* 2015; **3**: 3112–3129.
- 11 Philip N. State of the art enamel remineralization systems: The next frontier in caries management. *Caries Res* 2019; **53**: 284–295.
- 12 ten Cate JM, Buzalaf MAR. Fluoride mode of action: Once there was an bbservant dentist... *J Dent Res* 2019; **98**: 725–730.
- 13 ten Cate JM, Featherstone JDB. Mechanistic aspects of the interactions between fluoride and dental enamel. *Crit Rev Oral Biol Med* 1991; **2**: 283–296.
- 14 Pajor K, Pajchel L, Kolmas J. Hydroxyapatite and fluorapatite in conservative dentistry and oral implantology—A review. *Materials (Basel)* 2019; **12**: 2683.
- 15 Featherstone JDB, Glana R, Shariati M, Shields CP. Dependence of in vitro demineralization of apatite and remineralization of dental enamel on fluoride concentration. *J Dent Res* 1990; **69**: 620–625.
- 16 Cate JM ten. Current concepts on the theories of the mechanism of action of fluoride. *Acta Odontol Scand* 1999; **57**: 325–329.
- 17 Lippert F, Juthani K. Fluoride dose-response of human and bovine enamel artificial caries lesions under pH-cycling conditions. *Clin Oral Investig* 2015; **19**: 1947–1954.
- 18 Lippert F. Effect of enamel caries lesion baseline severity on fluoride dose-response. *Int J Dent* 2017; **2017**. doi:10.1155/2017/4321925.
- 19 Watson PS, Pontefract HA, Devine DA, Shore RC, Nattress BR, Kirkham J *et al*. Penetration of fluoride into natural plaque biofilms. *J Dent Res* 2005; **84**: 451–455.
- 20 Wong L, Cutress TW, Duncan JF. The Influence of Incorporated and Adsorbed Fluoride on the Dissolution of Powdered and Pelletized Hydroxyapatite in Fluoridated and Non-fluoridated

- Acid Buffers. *J Dent Res* 1987; **66**: 1735–1741.
- 21 Lynch RJM, Navada R, Walia R. Low-levels of fluoride in plaque and saliva and their effects on the demineralisation and remineralisation of enamel; role of fluoride toothpastes. *Int Dent J* 2004; **54**: 304–309.
- 22 Tokura T, Robinson C, Watson P, Abudiak H, Nakano T, Higashi K *et al.* Effect of pH on fluoride penetration into natural human plaque. *Pediatr Dent J* 2012; **22**: 140–144.
- 23 Rølla G. On the role of calcium fluoride in the cariostatic mechanism of fluoride. *Acta Odontol Scand* 1988; **46**: 341–345.
- 24 Øgaard B. Effects of fluoride on caries development and progression in vivo. *J Dent Res* 1990; **69**: 813–819.
- 25 González-Cabezas C, Fernández CE. Recent advances in remineralization therapies for caries lesions. *Adv Dent Res* 2018; **29**: 55–59.
- 26 Mäkinen KK. Sugar alcohols, caries incidence, and remineralization of caries lesions: A literature review. *Int J Dent* 2010; **2010**: 1–23.
- 27 Cummins D. The superior anti-caries efficacy of fluoride toothpaste containing 1.5% arginine. *J Clin Dent* 2016; **27**: 27–38.
- 28 Ástvaldsdóttir Á, Naimi-Akbar A, Davidson T, Brolund A, Lintamo L, Attergren Granath A *et al.* Arginine and caries prevention: A systematic review. *Caries Res* 2016; **50**: 383–393.
- 29 Fontana M. Enhancing fluoride: clinical human studies of alternatives or boosters for caries management. *Caries Res* 2016; **50**: 22–37.
- 30 Reynolds EC. Casein phosphopeptide-amorphous calcium phosphate: The scientific evidence. *Adv Dent Res* 2009; **21**: 25–29.
- 31 Hench LL. Bioceramics: From Concept to Clinic. *J Am Ceram Soc* 1991; **74**: 1487–1510.

- 32 Cerruti M, Greenspan D, Powers K. An analytical model for the dissolution of different particle size samples of Bioglass in TRIS-buffered solution. *Biomaterials* 2005; **26**: 4903–4911.
- 33 Burwell A, Jennings D, Muscle D, Greenspan DC. NovaMin and dentin hypersensitivity- In vitro evidence of efficacy. *J Clin Dent* 2010; **21**: 66–71.
- 34 Vahid Golpayegani M, Sohrabi A, Biria M, Ansari G. Remineralization Effect of Topical NovaMin Versus Sodium Fluoride (1.1%) on Caries-Like Lesions in Permanent Teeth. *J Dent (Tehran)* 2012; **9**: 68–75.
- 35 Liu X, Ding C, Chu PK. Mechanism of apatite formation on wollastonite coatings in simulated body fluids. *Biomaterials* 2004; **25**: 1755–1761.
- 36 Joiner A, Schäfer F, Naeeni MM, Gupta AK, Zero DT. Remineralisation effect of a dual-phase calcium silicate/phosphate gel combined with calcium silicate/phosphate toothpaste on acid-challenged enamel in situ. *J Dent* 2014; **42**: S53–S59.
- 37 Tung MS, Eichmiller FC. Dental applications of amorphous calcium phosphates. *J Clin Dent* 1999; **10**: 1–6.
- 38 Li L, Pan H, Tao J, Xu X, Mao C, Gu X *et al.* Repair of enamel by using hydroxyapatite nanoparticles as the building blocks. *J Mater Chem* 2008; **18**: 4079–4084.
- 39 Pepla E, Besharat LK, Palaia G, Tenore G, Migliau G. Nano-hydroxyapatite and its applications in preventive, restorative and regenerative dentistry: a review of literature. *Ann di Dtomatologia* 2014; **5**: 108–14.
- 40 Huang S, Gao S, Cheng L, Yu H. Remineralization potential of nano-hydroxyapatite on initial enamel lesions: An in vitro study. *Caries Res* 2011; **45**: 460–468.
- 41 Karlinsey RL, Mackey AC, Walker ER, Frederick KE. Surfactant-modified β -TCP: structure, properties, and in vitro remineralization of subsurface enamel lesions. *J Mater Sci Mater Med*

- 2010; **21**: 2009–2020.
- 42 Kirkham J, Firth A, Vernals D, Boden N, Robinson C, Shore RC *et al.* Self-assembling peptide scaffolds promote enamel remineralization. *J Dent Res* 2007; **86**: 426–430.
- 43 Kind L, Stevanovic S, Wuttig S, Wimberger S, Hofer J, Müller B *et al.* Biomimetic remineralization of carious lesions by self-assembling peptide. *J Dent Res* 2017; **96**: 790–797.
- 44 Silvertown JD, Wong BPY, Sivagurunathan KS, Abrams SH, Kirkham J, Amaechi BT. Remineralization of natural early caries lesions in vitro by P11-4 monitored with photothermal radiometry and luminescence. *J Investig Clin Dent* 2017; **8**: e12257.
- 45 Wierichs RJ, Kogel J, Lausch J, Esteves-Oliveira M, Meyer-Lueckel H. Effects of self-Assembling peptide P11-4, fluorides, and caries infiltration on artificial enamel caries lesions in vitro. *Caries Res* 2017; **51**: 451–459.
- 46 Kobeissi R, Osman E, Badr SB. Effectiveness of self-assembling peptide P11-4 compared to tricalcium phosphate fluoride varnish in remineralization of white spot lesions: A clinical randomized trial. *Int J Clin Pediatr Dent* 2021; **13**: 451–456.
- 47 Kondelova PS, Mannaa A, Bommer C, Abdelaziz M, Daeniker L, di Bella E *et al.* Efficacy of P11-4 for the treatment of initial buccal caries: a randomized clinical trial. *Sci Rep* 2020; **10**: 20211.
- 48 Hicks J, Garcia-Godoy F, Flaitz C. Biological factors in dental caries enamel structure and the caries process in the dynamic process of demineralization and remineralization (part 2). *J Clin Pediatr Dent* 2005; **28**: 119–124.
- 49 Kim Y, Son H-H, Yi K, Kim H-Y, Ahn J, Chang J. The color change in artificial white spot lesions measured using a spectroradiometer. *Clin Oral Investig* 2013; **17**: 139–146.
- 50 Hua F, Yan J, Zhao S, Yang H, He H. In vitro remineralization of enamel white spot lesions with a carrier-based amorphous calcium phosphate delivery system. *Clin Oral Investig* 2020; **24**:

- 2079–2089.
- 51 Ballard RW, Hagan JL, Phaup AN, Sarkar N, Townsend JA, Armbruster PC. Evaluation of 3 commercially available materials for resolution of white spot lesions. *Am J Orthod Dentofac Orthop* 2013; **143**: S78–S84.
- 52 Robinson C, Shore RC, Brookes SJ, Strafford S, Wood SR, Kirkham J. The chemistry of enamel caries. *Crit Rev Oral Biol Med* 2000; **11**: 481–495.
- 53 Milly H, Festy F, Watson TF, Thompson I, Banerjee A. Enamel white spot lesions can remineralise using bio-active glass and polyacrylic acid-modified bio-active glass powders. *J Dent* 2014; **42**: 158–166.
- 54 Flaitz CM, Hicks MJ. Remineralization of caries-like lesions of enamel with acidulated calcifying fluids: a polarized light microscopic study. *Pediatr Dent*; **18**: 205–9.
- 55 Gjorgievska ES, Nicholson JW, Slipper IJ, Stevanovic MM. Remineralization of demineralized enamel by toothpastes: A scanning electron microscopy, energy dispersive X-ray analysis, and three-dimensional stereo-micrographic study. *Microsc Microanal* 2013; **19**: 587–595.
- 56 Elkassas D, Arafa A. Remineralizing efficacy of different calcium-phosphate and fluoride based delivery vehicles on artificial caries like enamel lesions. *J Dent* 2014; **42**: 466–474.
- 57 Tomaz PLS, Sousa LA de, Aguiar KF de, Oliveira T de S, Matochek MHM, Polassi MR *et al*. Effects of 1450-ppm fluoride-containing toothpastes associated with boosters on the enamel remineralization and surface roughness after cariogenic challenge. *Eur J Dent* 2020; **14**: 161–170.
- 58 Wang Y, Mei L, Gong L, Li J, He S, Ji Y *et al*. Remineralization of early enamel caries lesions using different bioactive elements containing toothpastes: An in vitro study. *Technol Heal Care* 2016; **24**: 701–711.

- 59 Featherstone JDB. Consensus conference on intra-oral models: Evaluation techniques. *J Dent Res* 1992; **71**: 955–956.
- 60 Gängler P, Kremniczky T, Arnold WH. In vitro effect of fluoride oral hygiene tablets on artificial caries lesion formation and remineralization in human enamel. *BMC Oral Health* 2009; **9**: 25.
- 61 Amaechi BT, AbdulAzees PA, Alshareif DO, Shehata MA, Lima PP de CS, Abdollahi A *et al.* Comparative efficacy of a hydroxyapatite and a fluoride toothpaste for prevention and remineralization of dental caries in children. *BDJ Open* 2019; **5**. doi:10.1038/s41405-019-0026-8.
- 62 Damato FA, Strang R, Stephen KW. Effect of fluoride concentration on remineralization of carious enamel an in vitro pH-cycling study. *Caries Res* 1990; **24**: 174–180.
- 63 Cochrane NJ, Reynolds EC. Calcium phosphopeptides — mechanisms of action and evidence for clinical efficacy. *Adv Dent Res* 2012; **24**: 41–47.
- 64 Vieira AE de M, Danelon M, Camara DM da, Rosselli ER, Stock SR, Cannon ML *et al.* In vitro effect of amorphous calcium phosphate paste applied for extended periods of time on enamel remineralization. *J Appl Oral Sci* 2017; **25**: 596–603.
- 65 Bajaj M, Poornima P, Praveen S, Nagaveni N, Roopa K, Neena I *et al.* Comparison of CPP-ACP, tri-calcium phosphate and hydroxyapatite on remineralization of artificial caries like lesions on primary enamel -An in vitro study. *J Clin Pediatr Dent* 2016; **40**: 404–409.
- 66 Lendenmann U, Grogan J, Oppenheim FG. Saliva and dental pellicle-A review. *Adv Dent Res* 2000; **14**: 22–28.
- 67 Zhang J, Lynch RJM, Watson TF, Banerjee A. Remineralisation of enamel white spot lesions pre-treated with chitosan in the presence of salivary pellicle. *J Dent* 2018; **72**: 21–28.
- 68 Amaechi BT. Remineralisation - The buzzword for early MI caries management. *Br Dent J* 2017;

- 223**: 173–182.
- 69 Milly H, Festy F, Andiappan M, Watson TF, Thompson I, Banerjee A. Surface pre-conditioning with bioactive glass air-abrasion can enhance enamel white spot lesion remineralization. *Dent Mater* 2015; **31**: 522–533.
- 70 Zhang J, Boyes V, Festy F, Lynch RJM, Watson TF, Banerjee A. In-vitro subsurface remineralisation of artificial enamel white spot lesions pre-treated with chitosan. *Dent Mater* 2018; **34**: 1154–1167.
- 71 Lippert F. An introduction to toothpaste - Its purpose, history and ingredients. 2013, pp 1–14.
- 72 Sjögren K. How to improve oral fluoride retention? *Caries Res* 2001; **35**: 14–17.
- 73 Bakry AS, Abbassy MA. Increasing the efficiency of CPP-ACP to remineralize enamel white spot lesions. *J Dent* 2018; **76**: 52–57.
- 74 Cui F-Z, Ge J. New observations of the hierarchical structure of human enamel, from nanoscale to microscale. *J Tissue Eng Regen Med* 2007; **1**: 185–191.
- 75 Fincham AG, Moradian-Oldak J, Simmer JP. The structural biology of the developing dental enamel matrix. *J Struct Biol* 1999; **126**: 270–299.
- 76 Ruan Q, Zhang Y, Yang X, Nutt S, Moradian-Oldak J. An amelogenin–chitosan matrix promotes assembly of an enamel-like layer with a dense interface. *Acta Biomater* 2013; **9**: 7289–7297.
- 77 Ruan Q, Liberman D, Bapat R, Chandrababu KB, Phark J-H, Moradian-Oldak J. Efficacy of amelogenin-chitosan hydrogel in biomimetic repair of human enamel in pH-cycling systems. *J Biomed Eng Informatics* 2015; **2**: 119.
- 78 Hossein BG, Sadr A, Espigares J, Hariri I, Nakashima S, Hamba H *et al*. Study on the influence of leucine-rich amelogenin peptide (LRAP) on the remineralization of enamel defects via micro-focus x-ray computed tomography and nanoindentation. *Biomed Mater* 2015; **10**: 035007.

Table 1 Summary of non-fluoride based and biomimetic remineralisation technologies for enamel caries management (at the time of publication)

Technology	Remineralising mechanism	Advantages	Commercial products (company name)
<i>Calcium-phosphate systems</i>			
CPP-ACP	CPP amino acid sequences stabilise ACP to prevent crystal growth and provide mineral ions for later remineralisation	CPP-ACP can penetrate into subsurface and remineralise deep lesion	Tooth Mousse™/ MI Paste™ crème/ Recaldent™ (GC Corp.)
Bioglass (NovaMin)	Bioglass particles release Ca ²⁺ and PO ₄ ³⁻ as well as increase the pH via surface ion exchange	Fast release of ions and increase of pH can induce rapid deposition on lesion surface	Sensodyne™ Repair/ Oravive™ (GlaxoSmithKline)
ACP (Enamelon)	Unstable ACP releases bioavailable mineral ions before transformation to stable crystal phases	Bioavailable Ca ²⁺ and PO ₄ ³⁻ could transiently favour subsurface remineralisation	Enamelon™ (Premier Dental)
n-HA	n-HA particles bind to enamel defects, attracting Ca ²⁺ and PO ₄ ³⁻ to grow or acting as a reservoir	It has excellent biocompatibility and bioactivity due to similar morphology, structure and crystallinity to enamel crystals	Remin Pro™ (VOCO) Biorepair™ (Coswell)
f-TCP	f-TCP prevents premature reaction between Ca ²⁺ and fluoride, providing Ca ²⁺ for remineralisation	f-TCP can act as a targeted low-dose delivery system for remineralisation	Clinpro™ Toothpaste (3M)
<i>Biomimetic systems</i>			
Self-assembling peptides	SAPs act as an analogue to enamel matrix proteins to guide oriented apatite growth	SAP can diffuse into lesion body and attract ions for subsurface remineralisation	Curodont™ Repair (Credentis)
Amelogenin	Amelogenin proteins selectively bind to crystal facets to regulate oriented growth and react with ACP to form clusters that can later transform to HA	True biomineralisation with hierarchical structure is possible	Not available

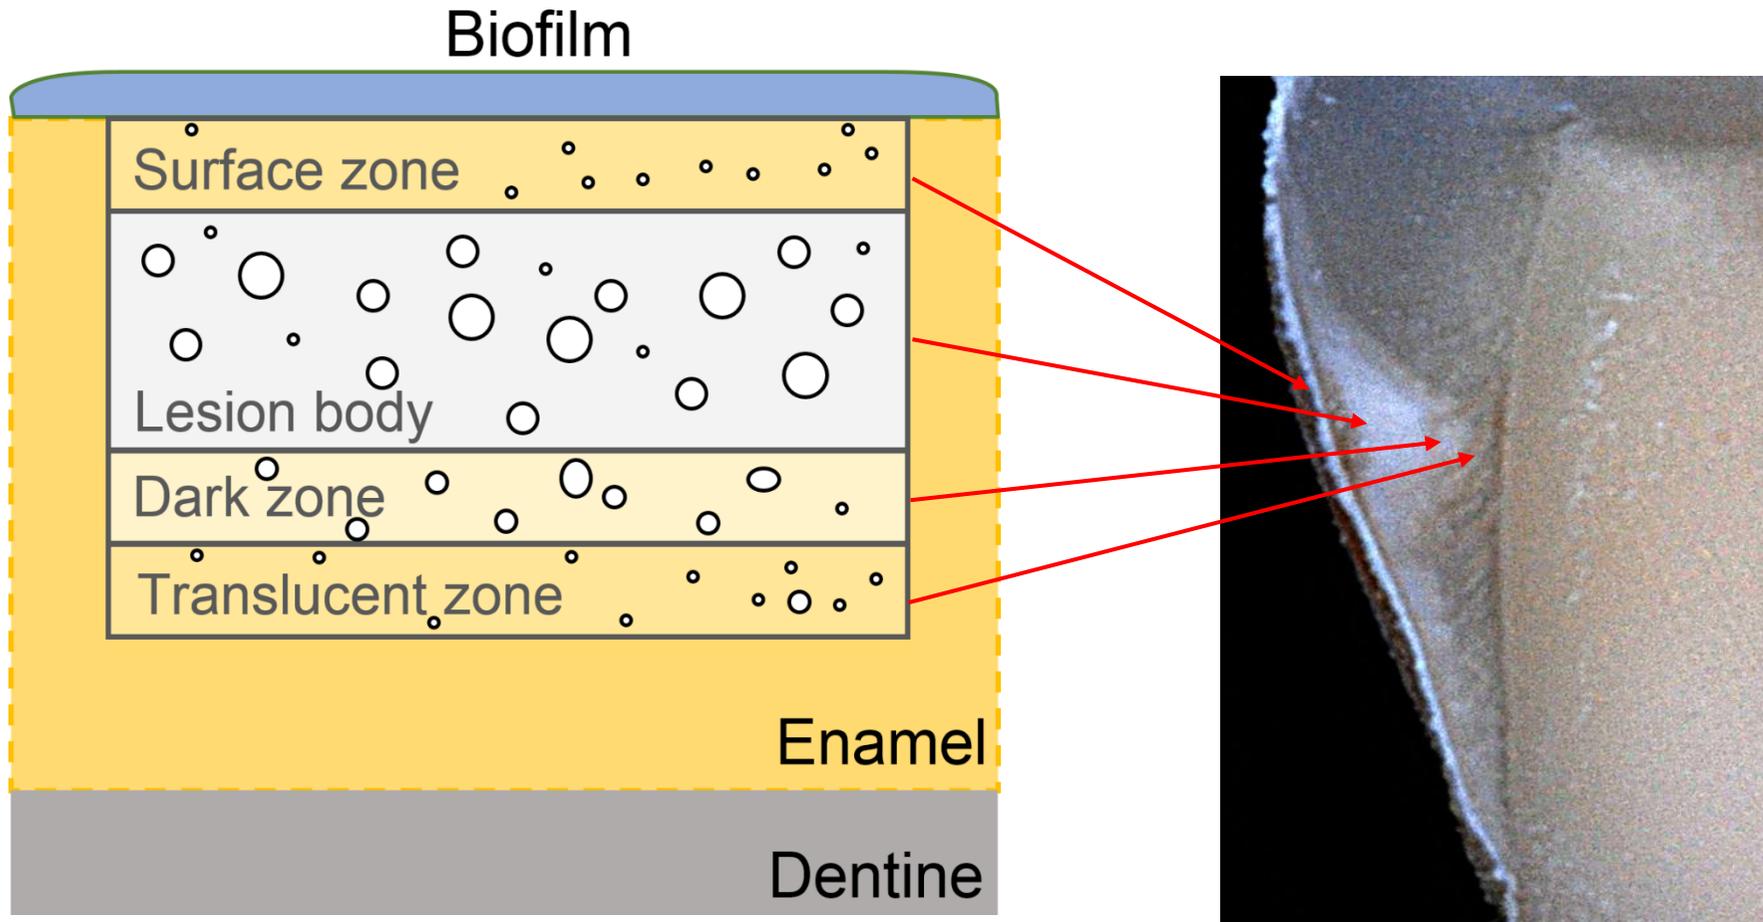


Figure 1 Basic histology (left) and clinical example (right, courtesy of L. Mackenzie) of an early enamel carious lesion. The enamel surface is covered by a layer of dental plaque biofilm, under which lies the surface zone with relatively small porosities which account for 1-2% vol. In contrast, the lesion body is more extensively demineralised with larger porosities (25-50%). Succeeding is the dark zone (porosity 5-10%) which shows a positive birefringence. Translucent zone has a similar porosity to the surface zone (1-2%) but the pore size is relatively larger which allows small molecules such as 2-chloronaphthalene or quinoline to penetrate⁵².

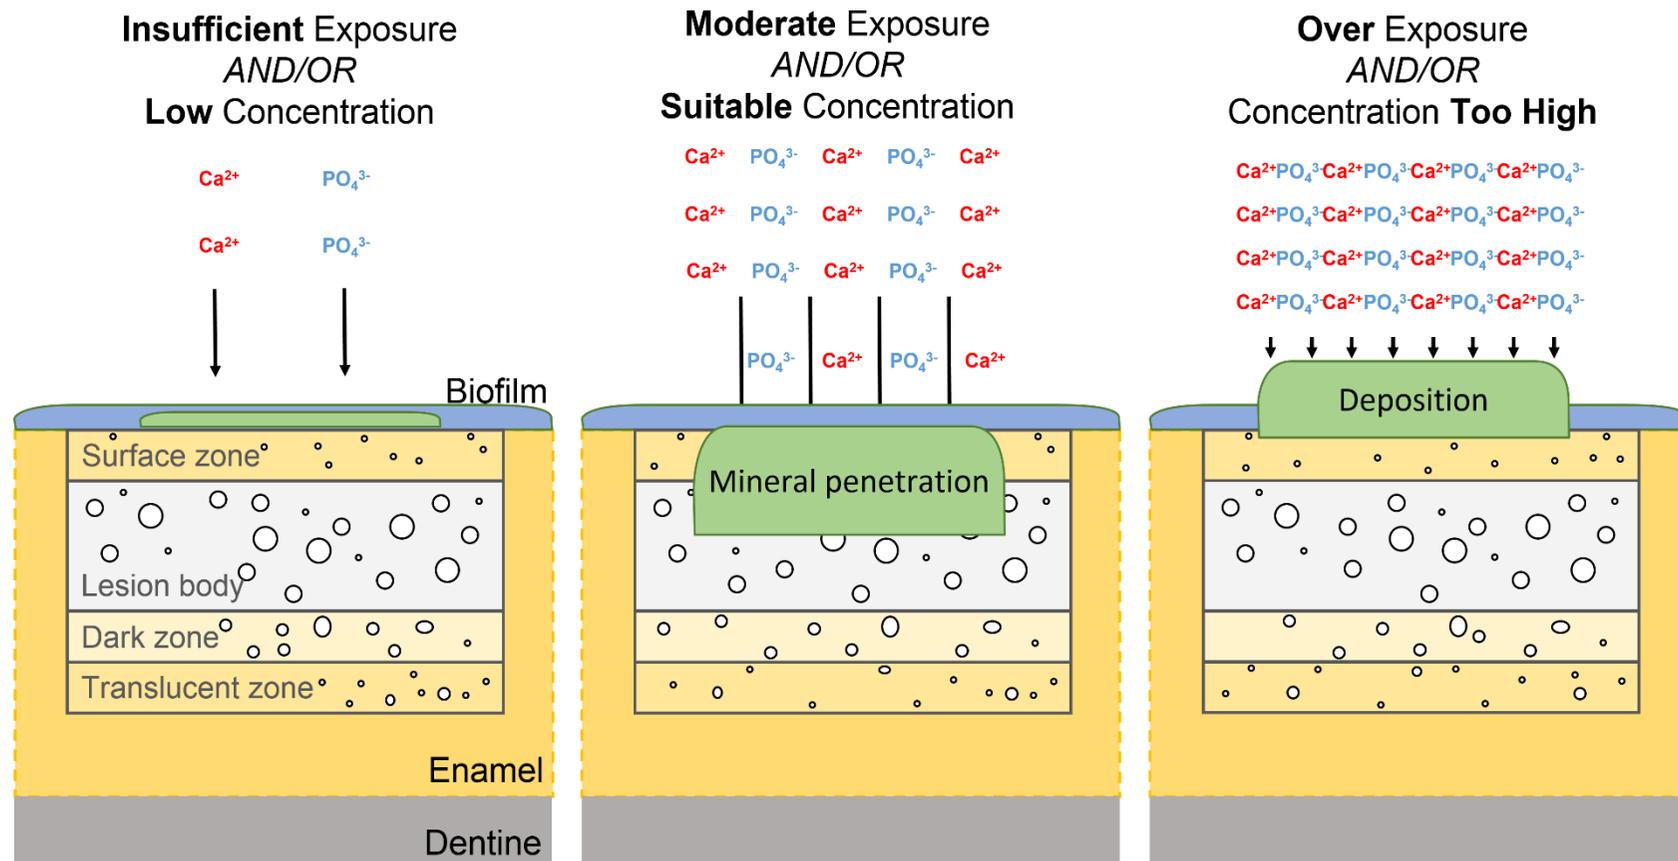


Figure 2 Illustration of basic mechanisms of remineralisation of the early carious lesion depending on calcium and phosphate exposure time as well as concentration in the biofilm adjacent to the tooth surface. The biofilm can reserve a portion of mineral ions, therefore providing buffering capacity and allow for an extended remineralisation. Excessive exposure time and/or concentration of mineral ions (left) would result in mineral deposition primarily on

the surface of the lesion whilst the subsurface remains untreated and the penetration of ions is hindered by the deposition. In comparison, insufficient exposure time and/or concentration (right) would result in small amount of mineral deposition on the surface. If the exposure time and/or concentration are controlled to be moderate, the subsurface of the lesion would be remineralised along with the surface, and the penetration of calcium phosphate ions would be allowed into depth.